

Evaluation of High Grade Recycled Coarse Aggregate Concrete Quality Using Non-Destructive Testing Technique

Ni Nyoman Kencanawati, **Jauhar Fajrin**, Buan Anshari, Akmaluddin, Mitsuhiro Shigeishi

Nama Jurnal	: Applied Mechanics and Materials
Volume Jurnal	: 776
Halaman	: 53-58
ISSN	: 1662-7482
Penerbit	: Trans Tech Publication
DOI (Opsional)	: 10.4028/www.scientific.net/AMM.776.53
Alamat Web Jurnal	: https://www.scientific.net/AMM.776.53
Terindex oleh	: Scopus (saat publikasi 2015, Scopus coverage 2005-2015) SJR, Copernicus, Cambridge Scientific EBSCO, ProQuest.
Quartile	: Q4 (saat publikasi, 2015)
SJR (2015)	: 0.11

Evaluation of High Grade Recycled Coarse Aggregate Concrete Quality Using Non-Destructive Testing Technique

Ni Nyoman Kencanawati^{1, a}, Jauhar Fajrin^{1, b}, Buan Anshari^{1, c}, Akmaluddin^{1, d}, and Mitsuhiro Shigeishi^{2, e}

¹Civil Engineering Department, Mataram University, Jl. Majapahit 62 Mataram, Indonesia

²Graduate School ²Graduate School Science and Technology, Kumamoto University, 2-39-1 Kurokami, Kumamoto, Japan

^ankencanawati@ts.ftunram.ac.id, ^bjauhar.fajrin@unram.ac.id, ^cbuan.anshari@ts.ftunram.ac.id, ^dakmal2k4@yahoo.co.uk, ^eshigeishi@civil.kumamoto-u.ac.jp

Keywords: non-destructive testing, hammer test, ultrasonic pulse velocity test, high grade recycled aggregate concrete.

Abstract. A large amount of waste concrete generates an environmental problem due to demolition of old concrete structures. To solve this problem, it is necessary to collect recycled aggregate from waste concrete. The conventional recycling technique of recycled aggregate from waste concrete does not indicate a significant quality to be re-used for making a new concrete. We proposed new techniques to produce high grade recycled aggregate by heating-grinding (H-G) method and heating-grinding-acid (H-G-A) method. To ensure the quality of the concrete made from recycled coarse aggregate concrete, the non-destructive evaluation was conducted in this research. High grade recycled aggregate concrete were prepared in advanced using two methods mentioned earlier. Then, new concrete specimens were produced using those types of recycled aggregate concrete. After 28 days curing time, rebound hammer test and ultrasonic pulse velocity test were performed on recycled coarse aggregate concrete to examine the surface hardness and ultrasonic wave velocity of the concrete. Almost similar quality to natural coarse aggregate in terms of density, water absorption, sieve analysis achieved by both H-G recycled coarse aggregate and H-G-A recycled coarse aggregate. However, the surface hardness and ultrasonic wave velocity of H-G-A recycled coarse aggregate concrete is better than those of H-G recycled coarse aggregate concrete. That acid solvent enables to dismantle the cement paste from aggregate surface more effectively, so this types of recycled aggregate shows a better performance than the other one. Continued delamination reduces pores in the interfacial transition zone resulting better bonding mechanism between new cement paste and recycled aggregate surface.

Introduction

The issue of waste concrete recycling has become more important in the world nowadays since construction wastes are increasing rapidly with the growth of the construction industry. After being produced, concrete is used to construct a concrete structure and provided to its user. When the service period of the structure is finished, the structure is demolished and disposed. Great disposal of concrete waste leads to environmental problem. In addition, significant exploitation of natural resources for concrete production is highly prohibited in some parts in the world. Thus, there is an urgent need to establish a recycling technology that reutilizes aggregate from concrete waste as a new material for fabrication of concrete in regard to environmental protection and optimized exploitation of resources. However, the conventional method of recycling does not meet the demand of recycled agregat to re-utilized for making a new concrete. This recycling process only produces smaller part from concrete lumps [1]. It only can be applied as road bed materials due to low quality of recycled aggregate. The surface of recycled aggregate is still attached by the old cement paste leading to low density and high water absorption of this aggregate.

To solve this problem, a new recycling technique has been developing in our laboratory using combination of thermal-mechanical-chemical techniques. Heating exposure up to 100°C – 200 °C weakens bonding between cement past and aggregate [2]. It should be noted that heating up to 500 °C does not affect the structure of the aggregate in concrete. After heating, the hot concrete lumps are then grinded to obtain the size of recycled aggregate. In addition, the recycled aggregate is soaked in acid solution to clean the residu of attached cement paste.

Before the recycled agregate manufactures will be used in, it needs to have the correct physical and mechanical properties. A series of research to examine the recycled agregate has been conducted. The high physical quality of recycled aggregate was obtained. Moreover, the new concrete produced by this type of recycled aggregate has an almost similar compressive strength to concrete made from normal agregate [3].

A non-destructive testing (NDT) was conducted in this research to gain more information about the properties of recycled coarse aggregate concrete produced by heating-grinding (H-G) method and heating-grinding-acid (H-G-A) method. A series of hammer test was applied to examine the surface hardness and ultrasonic pulse velocity test was employed to obtain the wave velocity of the recycled aggregate concrete. The results of these NDT are useful to evaluate the quality of the concrete.

Related Work

The use of recycled aggregate in producing new concrete is often associated with mechanical properties degradation of concrete. It is widely recognized that compressive strength in recycled aggregate concrete is lower than that of normal concrete with the same water-to-cement ratio. Concrete made from recycled aggregate has compressive strength - as much as 26% lower - than that of concrete made by natural aggregate [4]. An amount of attached cement paste reduces the interface adhesion between the recycled aggregate and the new cement paste; thus decreasing the mechanic strength of the concrete.

In Japan a new technology using pulsed power for concrete waste recycling has been developed. A promising result has been achieved because a greater amount of cement paste can be removed from aggregate without damaging the aggregate [5]. The attempt to reduce cement paste from aggregate surface also was studied using three pre-soaking treatment approaches; namely HCL, H₂SO₄ and H₃PO₄ [6].

The quality of concrete is often judged from its mechanical properties using concrete sample which need to be broken to obtain the properties. Non-destructive testing is potential to examine the inside the concrete such as layer and porosity. The study of fracture process in recycled aggregate concrete using acoustic emission has been published [7]. Concrete test hammers on concrete evaluate surface hardness as a function of resiliency, i.e., the ability of a hammer to rebound or spring back. Table 1 show the relationship between the average rebound number and the quality of concrete [8].

Table 1. Relationship between the average rebound number and the quality of concrete [8]

Average Rebound Number	Quality of Concrete
>40	Very good hard layer
30-40	Good layer
20-30	Fair
<20	Poor concrete
0	Delaminated

The pulse velocity method is appropriate for investigating of homogeneity of concrete, and, therefore, for relative assessment of quality of concrete. Heterogeneities in a concrete member will cause variations in the pulse velocity. The diffraction of a wave pulse around an internal air void will cause an increase in the time of propagation for an assumed path through the void center. Thus, the apparent velocity will decrease [8]. Table 2 indicates the relationship between velocity and concrete quality.

Table 2. Relationship between velocity and concrete quality [8]

UPV value in km/sec (V)	Concrete quality
V greater than 4.0	Very good
V between 3.5 and 4.0	Good, but may be porous
V between 3.0 and 3.5	Poor
V between 2.5 and 3.0	Very poor
V between 2.0 and 2.5	Very poor and low integrity
V less than 2.0 and reading fluctuating	No integrity, large voids suspected

Experiment

Material. There were several steps in producing recycled coarse aggregate. First, concrete lumps were heated up to 100°C for 24 hours. Second is mechanical grinding by 500 cycles using Los Angeles machine. These processes were objected to produce heating-grinding (H-G) recycled coarse aggregate. The addition treatment; which was soaked in acid solution (H₂SO₄) in 24 hours, was aimed to produce heating-grinding-acid (H-G-A) recycled coarse aggregate.

Then new concrete was made using two types of recycled coarse aggregate. For analysis consideration, normal fresh coarse aggregate concrete were also produced taken from the same query as material for recycling. Water cement ratio was 48%. Specimens were silinder concrete. Mixture proportion is shown in Table 3.

Table 3. Mixture proportion of concrete in 1 m³

Concrete type	Concrete ingredients (kg)			
	Cement	Water	Sand	Gravel
Normal coarse aggregate concrete	427	205	675	1013
H-G recycled coarse aggregate concrete	427	205	667	1001
H-G-A recycled coarse aggregate concrete	427	205	671	1007

Method. Rebound numbers were obtained by pushing hammer into the two flat surfaces of the silinder. The position of hammer was perpendicular to the surface of specimen. A rigid floor was used to ensure no sway occurring during the test. Five points reading were taken in each surface of silinder. Meanwhile, in ultrasonic pulse velocity measurement, the transmitter sensor was attached in one surface and receiver sensor was attached in other surface of specimen. Grease was used as a couplant to ensure good signal transmission between sensor and concrete. The velocity then can be read from the display.

Result and Discussion

Physical Properties of Recycled Aggregate. According to visual examination, in margin part of recycled coarse aggregate surfaces is still attached by cement paste. However, H-G-A recycled

coarse aggregate surfaces are much more cleaner than H-G recycled coarse aggregate surfaces. For further investigation, the quality examination of recycled aggregate includes density, water absorption, fineness modulus, and sieve analysis are examined. Almost similar properties are obtained compare to normal coarse aggregate, indicating the improvement quality of the recycled aggregate. Table 4 and Fig 1. show the properties of recycled coarse aggregate along with normal coarse aggregate as comparison.

Table 4. Properties of recycled coarse aggregate

Physical properties	Normal	H-G	H-G-A
Density	2,61	2,56	2,59
Water absorption(%)	1,23	2,62	2,43
Fineness Modulus	7,10	7,05	7,03

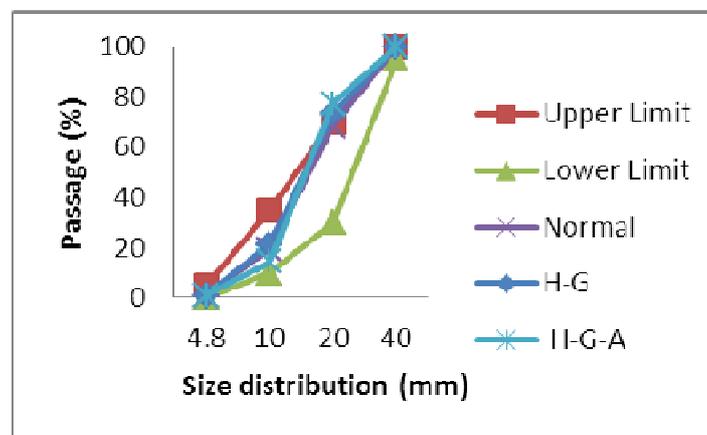


Fig. 1. Sieve analysis

Rebound Hammer Test. Concrete made of normal coarse aggregate possess the highest average rebound number. It is followed by the average rebound number of H-G-A recycled coarse aggregate concrete and that of H-G recycled coarse aggregate concrete respectively. Using H-G-A recycled coarse aggregate in concrete results better surface hardness than that of H-G recycled coarse aggregate. However, all the number falls in range of 30-40 meaning all the concrete is having good layer. Table 5 shows the average rebound number of the concrete.

Table 5. Average rebound number

Concrete type	Average Rebound Number
Normal concrete	37
H-G-A concrete	35
H-G concrete	34

Ultrasonic Pulse Velocity Test. Among the concrete types, the wave velocity of normal concrete is the greatest due to to good adhesive between cement paste and aggregate surface. H-G-A concrete shows better wave velocity around 5.5% than that of H-G concrete. According to Table 3 both recycled aggregate concrete indicate good quality. However, H-G-A concrete consists less porosity than that of H-G concrete. That acid solvent enables to dismantle the cement paste from aggregate surface more effectively, so this types of recycled aggregate shows a better performance than the other one. Continued delamination reduces pores in the interfacial transition zone resulting better

bonding mechanism occurs between new cement paste and recycled coarse aggregate surface. Fig 2 illustrates the wave velocity of each concrete type.

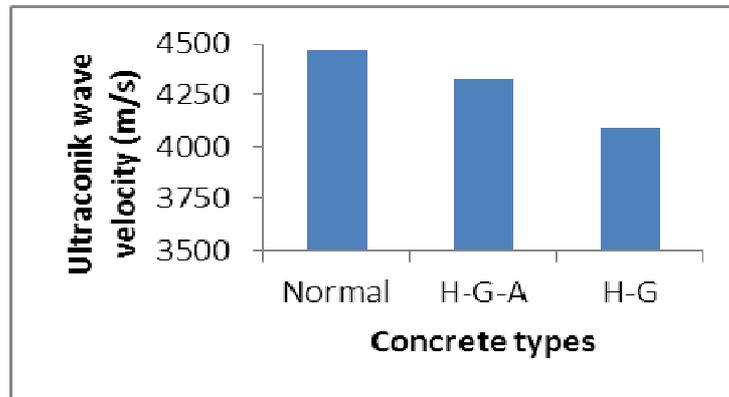


Fig. 2. Wave velocity of concrete.

Conclusion

Almost similar quality to natural coarse aggregate in terms of density, water absorption, sieve analysis achieved by both H-G recycled coarse aggregate and H-G-A recycled coarse aggregate. However, the surface hardness and ultrasonic wave velocity of H-G-A recycled coarse aggregate concrete is better than those of H-G recycled coarse aggregate concrete. That acid solvent enables to dismantle the cement paste from aggregate surface more effectively, so this type of recycled aggregate shows a better performance than the other one. Continued delamination reduces pores in the interfacial transition zone resulting in a better bonding mechanism occurring between new cement paste and recycled coarse aggregate surface.

Acknowledgement

This research has been funded by Mataram University through Post Graduate Program PNPB 2014 research grant.

References

- [1] Anwar SNR, Pemanfaatan Limbah Struktur sebagai Alternatif Pengganti Agregat Kasar Beton, e-Journal FT Unram, Vol 3(2007) 84-93 (in Indonesian).
- [2] Purkish JA, Fire Safety Engineering Design of Structures, Butterworth, Heinemann, 1996.
- [3] Hidayatturahman, Quality Improvement of Recycled Coarse Aggregate by of Heating, Grinding, dan Acid Method Combination , Master of Engineering Thesis, Post Graduate Program, Mataram University, 2014.
- [4] Xiao J., Li J., and Zhang C., Mechanical Properties of Recycled Aggregate Concrete under Uniaxial Loading, Cement and Concrete Research, vol. 35, issue 6 (2005), 1187-1194.
- [5] Narahara S., Namihira T., Nakashi K., Inone S., Iizasa S., Maeda S., Shigeishi M., Ohtsu M., and Akiyama H., Evaluation Of Concrete Made From Recycled Coarse Aggregates By Pulsed Power Discharge, Digest of Technical Paper- IEEE International Pulsed Power Conference (2007) 748-751.

[6] Tam, VWY, Tam CM, Le KN, Removal of Ceent Mortar Remains from Recycled Aggregate Using Pre-soaking approaches, Resources, Conservation, and Recycling, Vol 50, Issue 1(2007) 82-101.

[7] Kencanawati NN, Iizasa S, Shigeishi M, Fracture Process And Reliability Of Concrete Made From High Grade Recycled Aggregate Using Acoustic Emission Technique Under Compression, Materials and Structures, Volume 46, Issue 9 (2013), 1441-1448.

[8] Malhotra VM, and Carino NJ, Handbook on Non-destructive Testing of Concrete, CRC Press, USA, 2004.

**INFORMASI LENGKAP
ARTIKEL INI**



Source details

Applied Mechanics and Materials

Scopus coverage years: from 2005 to 2015

(coverage discontinued in Scopus)

Publisher: Scitec Publications Ltd.

ISSN: 1660-9336

Subject area: Engineering: General Engineering

SJR 2018

0.112



SNIP 2018

0.000



[View all documents >](#)

[Set document alert](#)

[Save to source list](#)

About Scopus

- [What is Scopus](#)
- [Content coverage](#)
- [Scopus blog](#)
- [Scopus API](#)
- [Privacy matters](#)

Language

- [日本語に切り替える](#)
- [切换到简体中文](#)
- [切换到繁體中文](#)
- [Русский язык](#)

Customer Service

- [Help](#)
- [Contact us](#)

ELSEVIER

[Terms and conditions ↗](#) [Privacy policy ↗](#)

Copyright © Elsevier B.V. ↗. All rights reserved. Scopus® is a registered trademark of Elsevier B.V.

We use cookies to help provide and enhance our service and tailor content. By continuing, you agree to the use of cookies.





Search



Paper Titles



Evaluation of High Grade Recycled Coarse Aggregate Concrete Quality Using Non-Destructive Testing Technique

981 18



Abstract:

A large amount of waste concrete generates an environmental problem due to demolition of old concrete structures. To solve this problem, it is necessary to collect recycled aggregate from waste concrete. The conventional recycling technique of recycled aggregate from waste concrete does not indicate a significant quality to be re-used for making a new concrete. We proposed new techniques to produce high grade recycled aggregate by heating-grinding (H-G) method and heating-grinding-acid (H-G-A) method. To ensure the quality of the concrete made from recycled coarse aggregate concrete, the non-destructive evaluation was conducted in this research. High grade recycled aggregate concrete were prepared in advanced using two methods mentioned earlier. Then, new concrete specimens were produced using those types of recycled aggregate concrete. After 28 days curing time, rebound hammer test and ultrasonic pulse velocity test were performed on recycled coarse aggregate concrete to examine the surface hardness and ultrasonic wave velocity of the concrete. Almost similar quality to natural coarse aggregate in terms of density, water absorption, sieve analysis achieved by both H-G recycled coarse aggregate and H-G-A recycled coarse aggregate. However, the surface hardness and ultrasonic wave velocity of H-G-A recycled coarse aggregate concrete is better than those of H-G recycled coarse aggregate concrete. That acid solvent enables to dismantle the cement paste from aggregate surface more effectively, so this types of recycled aggregate shows a better performance than the other one. Continued delamination reduces pores in the interfacial transition zone resulting better bonding mechanism between new cement paste and recycled aggregate surface.

ADD TO CART 

Diffusion Foundations

Nano Hybrids and Composites



Books



Special Book Collections



Specialized Collections

Retrospective Collection

Foundations of Materials Science and Engineering

Applied Mechanics and Materials - Details




ISSN: 1662-7482

Details

Volumes

Editorial Board

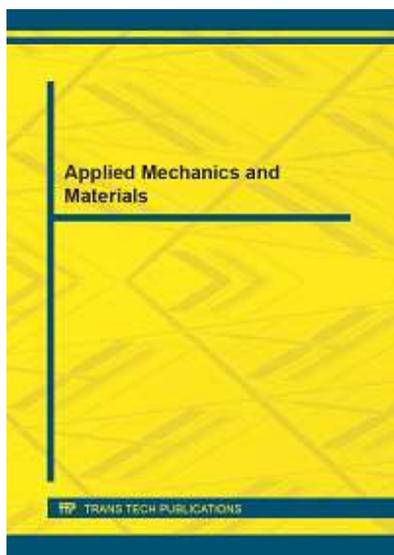

About:

"Applied Mechanics and Materials" is a peer-reviewed journal which specializes in the publication of proceedings of international scientific conferences, workshops and symposia as well as special volumes on topics of contemporary interest in all areas which are related to:

- 1) Research and design of mechanical systems, machines and mechanisms;
- 2) Materials engineering and technologies for manufacturing and processing;
- 3) Systems of automation and control in the areas of industrial production;
- 4) Advanced branches of mechanical engineering such as mechatronics, computer engineering and robotics.

"Applied Mechanics and Materials" publishes only complete volumes on given topics, proceedings and complete special topic volumes. We do not publish stand-alone papers by individual

authors.

Authors retain the right to publish an extended, significantly updated version in another periodical.

All published materials are archived with [PORTICO](#) and [CLOCKSS](#).

Presented, Distributed and **Abstracted/Indexed in:**

Inspec (IET, Institution of Engineering Technology) www.theiet.org.

Chemical Abstracts Service (CAS) www.cas.org.

Google Scholar scholar.google.com.

NASA Astrophysics Data System (ADS) <http://www.adsabs.harvard.edu/>.

Cambridge Scientific Abstracts (CSA) www.csa.com.

ProQuest www.proquest.com.

Ulrichsweb www.proquest.com/products-services/Ulrichsweb.html.

EBSCOhost Research Databases www.ebscohost.com/.

Zetoc zetoc.jisc.ac.uk.

Index Copernicus Journals Master List www.indexcopernicus.com.

WorldCat (OCLC) www.worldcat.org.

ISSN print 1660-9336 ISSN cd 2297-8941 ISSN web 1662-7482

Additional Information:

Please ask for additional information: amm@scientific.net

Subscription

Irregular: approx. 5-10 volumes per year.

Online Subscription Price 2021: EUR 1'200 / US\$ 1'380

- Access January-December 2021 to all Volumes published in 2021

- Published from 2004 - 2020: 902 Volumes

- Access on/via Scientific.net

Benefits to libraries: • Outright purchase • Perpetual access rights • Multiple concurrent users • Long-time preservation • COUNTER-compliant usage statistics • Pick & Choose licensing options as well as package options. • 24/7 access on www.scientific.net • Freedom to use offline or print • Advanced search options

Please contact us for all other subscription options, including access to backvolumes, multisite & archival licensing at subscriptions@scientific.net

Diffusion Foundations

Nano Hybrids and Composites



Books



Special Book Collections



Specialized Collections

Retrospective Collection

Foundations of Materials Science and Engineering

Applied Mechanics and Materials - Editorial Board



ISSN: 1662-7482

Details

Volumes

Editorial Board

Editor(s) in Chief

Prof. Xi Peng Xu



Huaqiao University, Research Institute of Manufacturing Engineering at Huaqiao University; No.668, Jimei Road, Xiamen, China, 361021;

Editorial Board

Prof. Ezio Cadoni



University of Applied Sciences of Southern Switzerland, Department for Construction, Environment and Design, DynaMat Laboratory, SUPSI-DACD; Campus Trevano, Canobbio, 6952, Switzerland;

Dr. Yuan Sheng Cheng



Harbin Institute of Technology, School of Materials Science and Technology; P.O. Box 435, Harbin, China, 150001;

Dr. Dmitry A. Chinakhov

National Research Tomsk Polytechnic University, Yurga Institute of Technology (Branch); Leningradskaya 26, Yurga, Russian Federation, 652055;

Prof. Oana Dodun

Gheorghe Asachi Technical University of Iași, Department of Machine Manufacturing Technology; D. Mangeron Blvd, 39A, Iași, 700050, Romania;

Prof. Grigore Gogu

Institut Français de Mécanique Avancée, Campus de Clermont-Ferrand/les Cézeaux, CS 20265; Clermont-Ferrand, 63175, France;

Dr. Tibor Krenický

Technical University of Košice, Faculty of Manufacturing Technologies with a Seat in Prešov; Bayerova 1, Presov, 080 01, Slovakia;

Dr. Rozli Zulkifli

Universiti Kebangsaan Malaysia, Department of Mechanical and Materials Engineering, Faculty of Engineering and Built Environment; Bangi, Malaysia, 43600;

DISTRIBUTION & ACCESS

FOR PUBLICATION

INSIGHTS

DOCU CENTER

ABOUT US

POLICY & ETHICS

CONTACT US

IMPRINT

PRIVACY POLICY

SITEMAP





Publish articles in 1 day

Open Access, International Journals, High Citation, Indexed Journals

noveltyjournals.com

OPEN

Applied Mechanics and Materials

discontinued in Scopus as of 2014

Country [Switzerland](#) - [IIII](#) [SJR Ranking of Switzerland](#)

Subject Area and Category [Engineering](#)
[Engineering \(miscellaneous\)](#)

Publisher [Trans Tech Publications](#)

Publication type [Book Series](#)

ISSN [16609336](#)

Coverage [2005-2015](#)

Scope "Applied Mechanics and Materials" is a peer-reviewed journal which specializes in the publication of proceedings of international scientific conferences, workshops and symposia as well as special volumes on topics of contemporary interest in all areas which are related to: 1) Research and design of mechanical systems, machines and mechanisms; 2) Materials engineering and technologies for manufacturing and processing; 3) Systems of automation and control in the areas of industrial production; 4) Advanced branches of mechanical engineering such as mechatronics, computer engineering and robotics. "Applied Mechanics and Materials" publishes only complete volumes on given topics, proceedings and complete special topic volumes. We do not publish stand-alone papers by individual authors.



[Homepage](#)

[Contact](#)



[Join the conversation about this journal](#)

29

H Index


Publish articles in 1 day

Open Access, International Journals, High Citation, Indexed Journals


noveltyjournals.com

OPEN


Quartiles

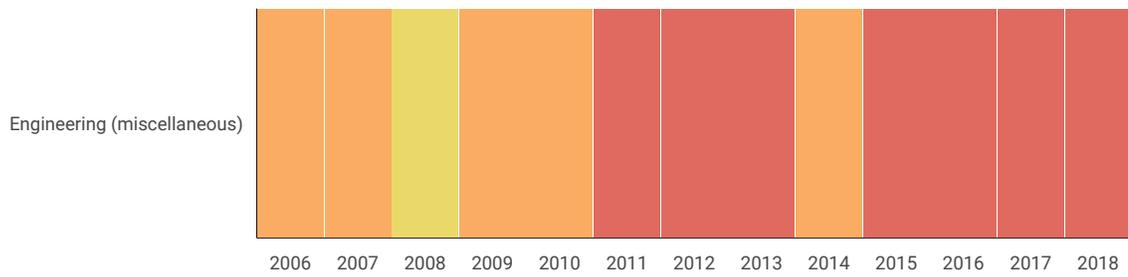


SJR

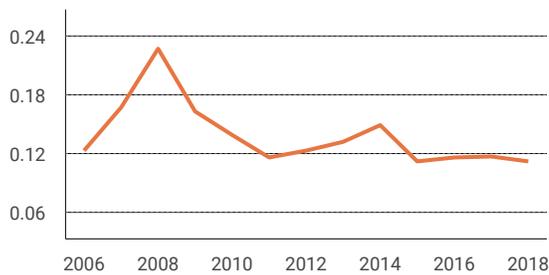


Citations per document

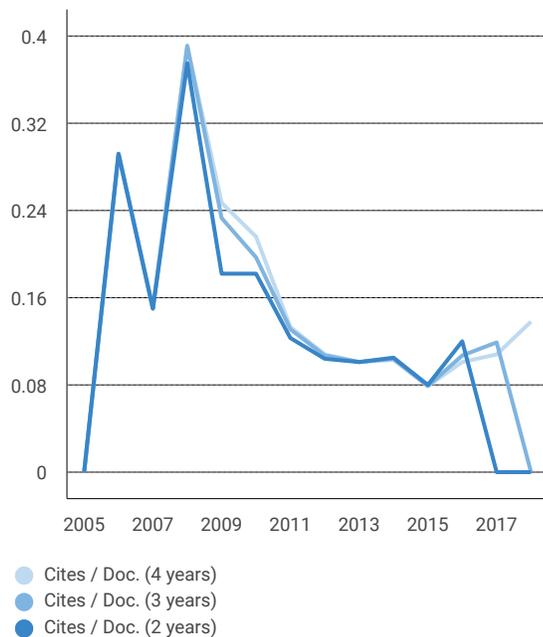


Total Cites / Self-Cites

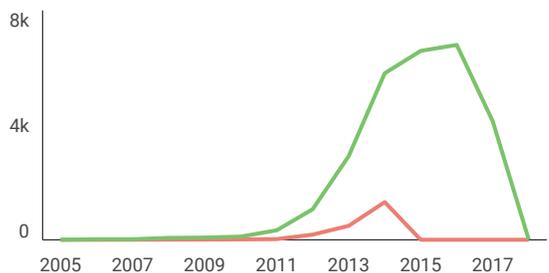

External Cites per Doc / Cites per Doc

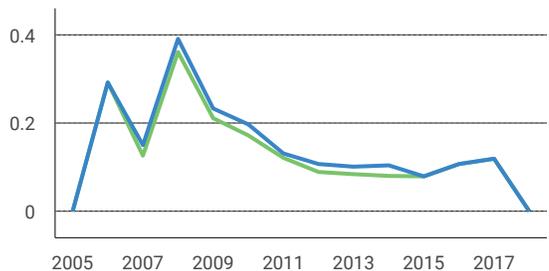

% International Collaboration


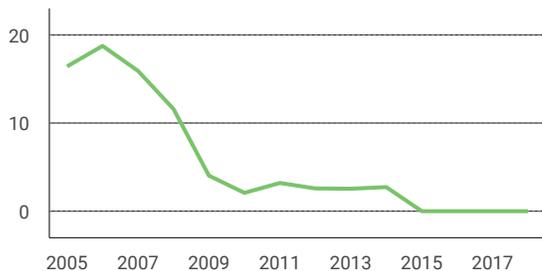


Citable documents / Non-citable documents




Cited documents / Uncited documents



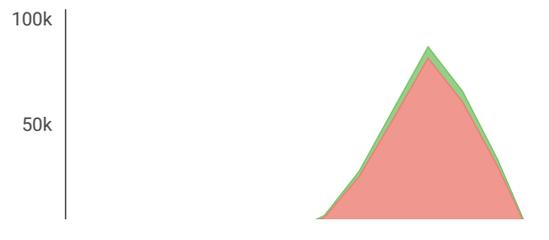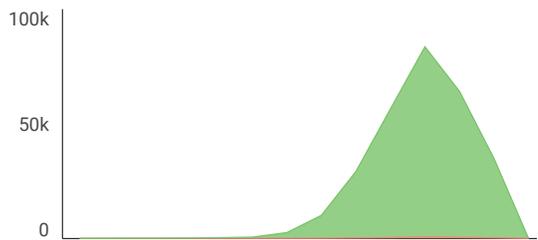

Applied Mechanics and Materials

Not yet assigned quartile



← Show this widget in your own website

Just copy the code below and paste within your html code:

```
<a href="https://www.scimaç
```

Study Mechatronics at IULI

Spend up to one year in Germany for a study, research & internship.

iuli.ac.id

OPEN

P

pandi mani 7 months ago

dear sir/mam,

myself a Ph.D scholar in civil engineering, i wish to publish my research paper to this journal.

- 1) Now i wish to know whether it is a scopus/ sci indexed one or not.
- 2) if yes, then is there any journal processing fees to be paid.
- 3) how long (duration in months)it take to be accept and publish the paper.

THANK YOU,
REGARDS,
PANDIMANI.

← reply



Melanie Ortiz 7 months ago

SCImago Team

Dear Pandimani, thank you very much for your comment, unfortunately we cannot help you with your request. We suggest you to consult the Scopus database directly. Remember that the SJR is a static image of a database (Scopus) which is changing every