

Recycled Powder Concrete

by Civil Engineering Department Mataram University

Submission date: 17-Aug-2021 06:50PM (UTC+0700)

Submission ID: 1632437934

File name: Ni_Nyoman_Kencanawati_et_al.pdf (714.01K)

Word count: 3831

Character count: 19961

The Role of Recycling Waste Powder as a Sustainable Concrete Manufacturing Material

Ni Nyoman Kencanawati^{1,a)}, Miko Eniarti^{1,b)}, and Dedi A Alfarizi^{1,c)}

¹Civil Engineering Department, Mataram University, Jl. Majapahit 62, 83125 Indonesia

^{a)} Corresponding author: nkencanawati@unram.ac.id

^{b)} mikoeniarti@gmail.com

^{c)} alfarizidedi1998@gmail.com

Abstract. The production of high-quality recycled aggregate from waste concrete provides a by-product in the form of a powder. It has been separated from the surface of the aggregate during a grinding process. The properties of the powder and its application as a material in the manufacture of concrete were investigated in this study. It is expected that this powder waste can be used sustainably in concrete manufacturing. The testing procedure included an investigation of the chemical, physical, and mechanical properties of the concrete waste powder. Furthermore, the powder was used both as a substitute for Portland cement by 25% and 50% and as an addition of Portland cement by 5%. The initial setting time, final setting time, and the consistency of the recycled waste concrete powder are greater than that of Portland cement. The increase also occurs in the chemical content of silica oxide and iron oxide. Furthermore, the strength activity index shows a value of 76.5%. Concrete with a substitution of 25% and 50% of waste concrete powder shows a decrease in compressive strength of 23.54% and 42.84%, respectively, compared to the normal compressive strength. Meanwhile, the addition of concrete waste powder to concrete with an addition of 5% reaches an increase in compressive strength of 22.98%. The use of waste concrete powder is recommended as an additional material because it can perform as a filler; consequently, it produces denser concrete.

INTRODUCTION

Concrete is a construction material that is widely used in building structural work because of many advantages it provides, including the constituent materials that are easy to obtain, easy to form, cheaper, do not require special treatment, and are more resistant to the weather [1]. Almost all the materials used for the manufacture of concrete use materials from nature so that with the use of large concrete, huge mining of natural rock as a concrete-forming material occurs; as a result, the production of concrete is becoming more expensive. Furthermore, the high demand for cement in the manufacture of concrete is one of the background problems in the current construction industry. It is known that excessive use of cement is one of the things that cause global warming. Therefore the reuse of waste as a substitute and added to the use of cement is very necessary [2], [3].

Another issue that has been arising that the demolition of concrete construction due to aging causes a very large amount of concrete waste. The demolition of concrete construction due to aging causes a very large amount of concrete waste [4]–[7]. The technique of recycling concrete waste is an alternative in reducing the negative impact due to the accumulation of concrete waste on the environment. Extracting coarse aggregate from the concrete waste lump is a method to produce recycled aggregate. Higher quality recycled aggregate demands a clean surface from the surrounding old mortar [6], [8]–[13]. Therefore, during the production process of higher quality recycled aggregate, a large amount of powder has been generated as the a-side product.

Several researchers have conducted a study on waste concrete powder [14]–[17]. In [16] using waste concrete powder in cement mortar. It was found that the compressive strength of the mortar became lower when the higher the amount of waste concrete powder used as a cement substitute. The compressive strength of mortar with powdered waste concrete is reduced by up to 73% compared to mortar with Portland cement. Similarly result has been found other research on the cementitious properties of this concrete waste powder. Some components in the

waste concrete powder are non-reactive so they cannot effectively act as cement. However, for the sake of the environment, research continues to be developed so that this material can be used as a material for making new concrete. Thus, this research will comprehensively study the properties of this waste concrete powder and its application to materials, either as a substitute for cement or as an additive in concrete mixtures. Concrete waste powder which is a by-product of recycling the quality of aggregates with the thermal-mechanical method developed at the structure laboratory of the University of Mataram can be used as an ingredient for sustainably concrete [10], [11].

THEORY

Waste Concrete Recycling Process

The conventional process of recycling concrete is by breaking the large concrete lump to be a smaller pieces resembling as coarse recycled aggregate. However, due to large amount of attached mortar, the utilization has not well developed. Along with the development of technology, the process of recycling the concrete is also developed using several methods. All the methods have been dedicated to obtain high quality of recycled aggregate in which free from the old cement paste in the surfaces. One of the methods in waste concrete recycling process is using combination of heating and grinding method.

Heating at a temperature of 100° C is intended to achieve evaporation of water contained in the pores of the mortar; therefore it causes pressure in the mortar which facilitates the release of the mortar from the aggregate [18]. Then the heated concrete is brought into grinding process. Grinding is effective for breaking the concrete and separating the attached mortar from recycled concrete. This method is usually carried out with a machine that rotates at a certain speed so that this rotation is intended to assist the release of mortar in the aggregate [11].

During the manufacturing process of high quality recycled aggregate, 15-30% of powder waste is generated [14]. To be able to utilize this powder waste, further research is needed because so far research on concrete waste has focused more on the production of recycled aggregates.

Physical Properties Testing

Physical test of concrete waste powder involves testing of normal consistency and setting time. The testings are conducted by performing a Vicat test. A normal consistency test is aimed to obtain the appropriate water content in a mixing. The normal consistency is greatly influenced by the amount and type of cementitious material used. Normal consistency is achieved when the Vicat needle can penetrate the paste 10 ± 1 mm within 30 seconds after needle removal. The setting time test was carried out by determining the time of penetration is obtained by 25 mm for the initial setting time. Meanwhile, the final setting time is when the needle does not appear to be immersed in the paste.

The initial setting time on ordinary Portland cement is required not less than 60 minutes and the final setting time is not more than 480 minutes.

A reasonably long initial setting time is needed to allow the concrete maker to work on the concrete manufacturing process, namely mixing, pouring, compacting, and leveling the surface. For a shorter setting time, it is intended to provide faster hardening of the concrete, so that a construction work can be completed more quickly due to the easier drying process [19], [20].

Mechanical Properties Testing

To investigate the mechanical properties of concrete is mainly through a testing under a compression load. In this testing the modulus elasticity of concrete can be also determined. According to SNI 03-1974-1990 [21], the compressive strength of concrete is the maximum magnitude of the compression load per unit area, which causes the concrete cylinder specimen to be a failure. The compressive load is generated by a compression testing machine with a load rate of 0.2 MPa/second. The maximum compressive strength f_c is given by Eq. 1:

$$\sigma = \frac{P}{A} \quad (1)$$

Where σ is compressive strength (MPa), P is the maximum magnitude of compression load (N), and A is the cross section of cylinder concrete (mm^2).

The modulus of elasticity of concrete is determined by dividing the value of the stress by the strain during an elastic area. The condition is determined when the stress reaches 40% of the compressive strength. The equation of the modulus of elasticity according to the code is presented in Eq. 2 [21].

$$E_c = \frac{S_2 - S_1}{\epsilon_2 - 0,00005} \quad (2)$$

Where E_c is modulus of elasticity (MPa), S_2 is stress at $0.4f_c$, S_1 is stress at strain due to of 0.00005 (MPa), and ϵ_2 is strain due to stress S_1 .

METHODOLOGY

Material

Concrete waste powder was generated from a production of recycled aggregate using heating and grinding method. Preparation of the waste concrete powder material begins with cutting the waste concrete into approximately 20-30 cm. These pieces are put in an oven for 24 hours at a temperature of 100 C. This process is intended to weaken the bond of cement paste to the aggregate surface. In hot conditions, this concrete waste is taken to a crushing machine to get aggregates that are of appropriate size and free from cement paste. The remaining cement paste in the form of powder is under the machine and collected for use in this study. Furthermore, the powder is checked for fineness to match the requirements as a pozzolan, namely passing on a No 200 sieve with the amount of material passing more than 70%. This process is shown in Figure 1.



FIGURE 1. Waste concrete generation during recycled aggregate production

Concrete specimens were made from waste concrete powder by using it as a substitute for cement and also as an additive to the concrete mixture. As a substitute for cement, percentages of 25% and 50% were used because it is desirable to use waste material as much as possible for the benefit of the environment. As much as 5% of the powder was used in the concrete mix as an additive. Concrete specimens with a binder of 100% Portland cement and 100% concrete waste powder were also prepared as control specimens. The variation of the test object is shown in Table 1.

TABLE 1. Specimens variation

Semen Type	Role	Proportion in Concrete Mixture
		(%)
Portland Cement		100
Recycling	Subtitutive	25
		50
		100
	Additive	5

Fine aggregate and coarse aggregate used in concrete mixtures had a maximum diameter of 4.75 mm and 20 mm. Fine aggregate is natural aggregate and coarse aggregate is crushed stone. The specific gravity of fine aggregate and coarse aggregate were 2.82 and 2.76, respectively. The properties of aggregates met the requirement from the

national code of aggregate for concrete [22]. The results of the sieve analysis of the aggregates used can be seen in Figure 2.

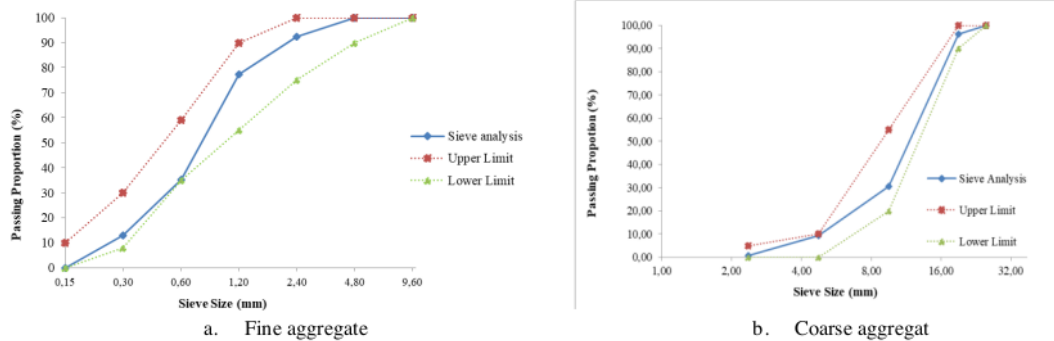


FIGURE 2. Sieve analysis

The calculation of the mixed design is based on the national standard SK.SNI.T-15-1990-03 with the water-cement factor value set at 0.5. The need for control concrete with 100% Portland cement is shown in Table 3. Furthermore, the need for waste concrete powder is proportional to the weight of Portland cement-based on the percentages that have been set in Table 1.

TABLE 2. Concrete mixture proportion


Concrete Ingredient	Proportion (kg/m ³)
Water	225
Portland cement	450
Fine aggregate	817
Coarse aggregate	959

Testing

The test consists of two aspects, namely testing of waste concrete powder material and testing of concrete. Testing of waste concrete material includes testing on chemical composition, testing for normal consistency, testing for initial setting time, and testing for final setting time. The concrete specimens are cylindrical in sizes 150 mm and 300 mm. Tests on concrete include testing the properties of fresh concrete and the mechanical properties of concrete. The compressive strength of the elastic modulus of concrete is examined by the mechanical properties of concrete. Figure 3-4 shows the intended concrete test.



FIGURE 3. Fresh properties of testing concrete

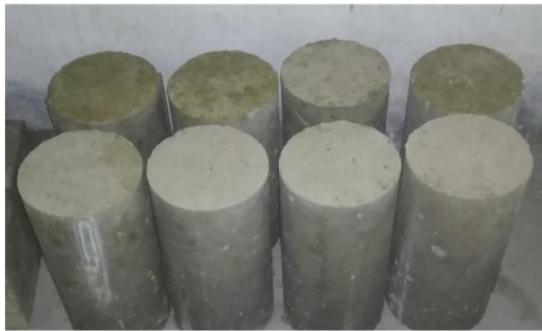

a. Some of the specimens



b. Compressive testing

FIGURE 4. Specimens and concrete testing

RESULT AND DISCUSSIONS

Chemical Composition

From the results of testing the content of chemical compounds on cement and concrete waste powder, the percentage of iron compounds (Fe_2O_3) in concrete waste powder is higher by 3.23% compared to Portland Composite Cement (PCC) of 2.91%. The content of iron (Fe_2O_3) in cement and powdered concrete waste has met the specified percentage value, which is 0.5%-6% [1].

The increase in the iron content (Fe_2O_3) in the concrete waste powder is due to the cement, sand, and crushed stone in the recycled concrete waste still containing iron (Fe_2O_3) so that in the grinding process the iron (Fe_2O_3) content in cement, sand, and crushed stone is increased. combined into a constituent of concrete waste powder. As for the function of iron (Fe_2O_3) itself in cement, namely as a forming compound of Tetracalcium Aluminoferrite (C_4AF) or $4\text{CaO} \cdot \text{Al}_2\text{O}_3 \cdot \text{Fe}_2\text{O}_3$. The C_4AF compound has less effect on the hardness of cement or concrete so that its

contribution to the increase in strength is small but has sufficient or moderate heat hydration so that it hydrates quickly.

Physical Properties

There was an increase in the need for water as the increasing proportion of the use of powdered concrete waste as a substitute material. This is because the concrete waste powder absorbs more water during the mixing process. The consistency for Portland cement is found 24.5%. Waste concrete powder requires 1.6 times more water to achieve normal consistency than Portland cement. As a substitute for 25% cement, waste concrete powder requires almost the same water as Portland cement with a normal consistency of 26% as shown in Table 3.

TABLE 3. Normal consistency

Role	Proportion in Concrete Mixture	Normal Consistency
	(%)	(%)
Portland Cement	100	24,5
Powder as Subtitutive	25	26
	50	31
	100	39
Powder as Additive	5	25,5

As an additive, waste concrete powder has a water requirement to reach a normal consistency of 25.5%. This amount is also not significantly different from the normal consistency of Portland cement. This is considered because the addition of concrete waste powder is relatively small at 5%. In order to maintain a consistent normal consistency in the increasing proportion of concrete waste powder as an additive, it is recommended to add a superplasticizer to the mixture.

Based on Figure 5, the initial setting time of Portland Cement is faster than that of waste concrete powder in which an initial setting time of 105 minutes and a final setting time of 150 minutes. These values are increasing when the waste concrete powder is utilized as the binder entirely in the mixing. The initial setting time is increasing to 180 minutes and the final setting time escalates to 255 minutes. As seen from the graph, there is an increase in the initial and final setting time along with the increasing use of waste concrete powder as a substitute material, because the waste concrete powder has a lesser binding strength.

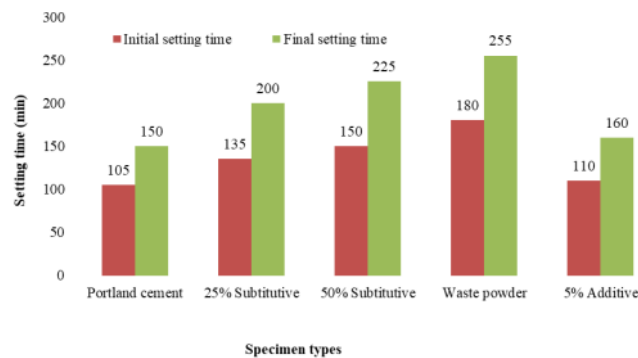


FIGURE 5. Specimens and concrete testing

Based on the test results of the setting time of Portland cement and waste powder, it shows that the two materials have met the requirements as a concrete mixture according to the requirements for the initial setting time on

Portland cement not less than 60 minutes and the final bonding time should not be more than 480 minutes (Tjokrodimaljo, 2007).).

Fresh Concrete Properties

The greatest slump occurs on normal concrete with Portland cement binder. The slump is 6.8 cm. This value drops to 4.5 cm when all portion of Portland cement is replaced by waste powder. The slump decreases to 11.76% and 23.53% in 25% and 50% substitutive of waste powder concrete respectively. The lower slump value occurs on the concrete with waste concrete powder binder due to higher water absorption was occurring during the mixing.

The slump of the concrete with 5% waste powder addition gives a zero slump; however to make it easier to work a superplasticizer was added to the mixing. As the result, a slump of 7 cm is obtained

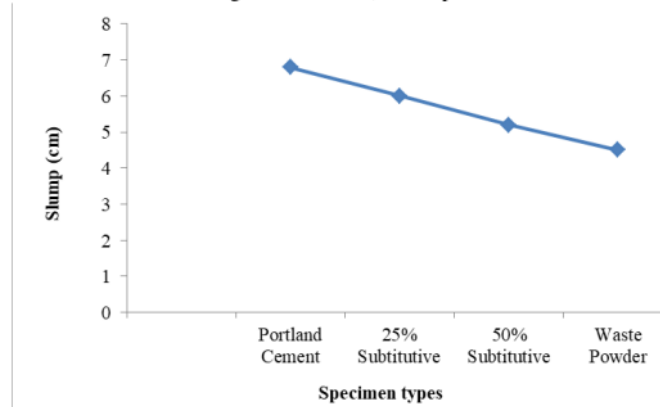


FIGURE 6. Fresh concrete slump

Mechanical Properties

Judging from the compressive strength of normal concrete of 27.15 MPa and concrete with a mixture of 25% waste powder the value of compressive strength is 20.76 MPa, there is a decrease in the value of compressive strength by 23.54%. For the value of the compressive strength of concrete with a mixture of 50% waste powder of 15.52 MPa there is a decrease in the compressive strength value of 42.84%. The decrease is getting greater for the whole waste powder as the cementitious material in concrete. The decrease in the value of the compressive strength of concrete occurs because the waste concrete powder does not have a strong binding capacity like cement in general.

Meanwhile, for concrete with waste powder as added material, the compressive strength value is 33.39 MPa, an increase in compressive strength of 22.98% from normal concrete. This is because the concrete waste powder as an added ingredient can fill the pores in the concrete so that the concrete becomes denser and the compressive strength value is high. Similar to compressive strength, the modulus elasticity is considered has the same trend due to the role of the waste powder in concrete. Figure 7 shows the concrete mechanical properties

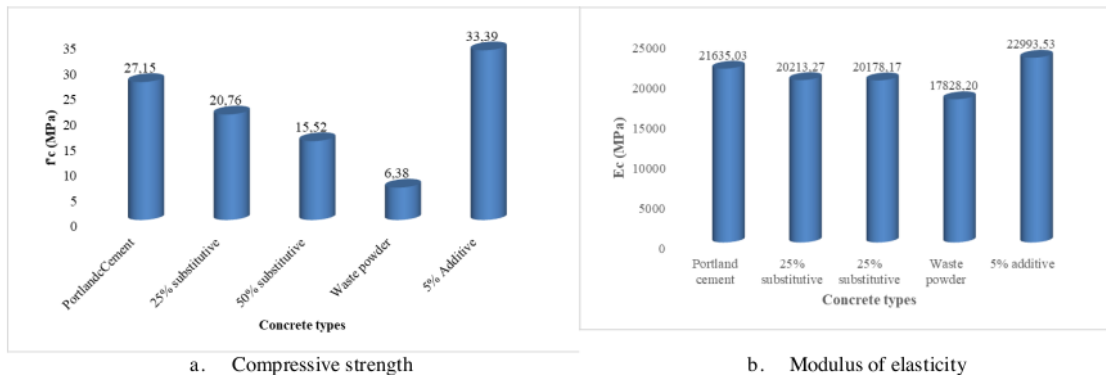


Figure 7. Mechanical properties

CONCLUSION

The results of the concrete compressive strength test show a decrease in each increase in the concentration of the mixed concrete waste powder as a substitute for cement used. For concrete with a mixture of 25%, 50%, and 100% waste powder, there was a decrease of 23.54%, 42.84%, and 76.50% respectively for normal concrete. While the waste powder as an added material by 5% experienced an increase of 22.98% against normal concrete.

The results of testing the modulus of elasticity of concrete are directly proportional to the results of the compressive strength test, the results show a decrease in each increase in the concentration of the waste powder mixture as a cement substitute. In the mixture with 25%, 50%, and 100% waste powder, the modulus of elasticity decreased by 6.57%, 6.73%, and 17.59%, respectively. Meanwhile, for waste powder as an added material, 5% increased by 6.28% compared to normal concrete.

The test results of the split tensile strength of concrete are the same as the compressive strength and modulus of elasticity. For the value of the split tensile strength with a mixture of 25% and 50% waste powder, the decrease was 9.36% and 25.44%, respectively, of the split tensile strength of normal concrete.

The use of waste concrete powder as a substitute for cement does not increase the quality value of concrete, because the waste concrete powder does not have a strong binding capacity like cement in general. While the concrete waste powder as an added material provides an increase in the quality value of concrete because the concrete waste powder can fill the pores of the concrete so that the concrete becomes solid.

REFERENCES

- [1] K. Tjokrodinuljo, *Concrete Technology (in Indonesian)*. Yogyakarta: Nafiri, 2007.
- [2] S. Mindess, "1 - Sustainability of concrete," in *Developments in the Formulation and Reinforcement of Concrete (Second Edition)*, Second Edition, S. Mindess, Ed. Woodhead Publishing, 2019, pp. 3–17.
- [3] L. Assi, K. Carter, E. (Eddie) Deaver, R. Anay, and P. Ziehl, "Sustainable concrete: Building a greener future," *J. Clean. Prod.*, vol. 198, pp. 1641–1651, 2018, doi: <https://doi.org/10.1016/j.jclepro.2018.07.123>.
- [4] F. Pacheco-Torgal, "1 - Introduction to advances in construction and demolition waste," in *Advances in Construction and Demolition Waste Recycling*, F. Pacheco-Torgal, Y. Ding, F. Colangelo, R. Tuladhar, and A. Koutamanis, Eds. Woodhead Publishing, 2020, pp. 1–10.
- [5] K. Kabirifar, M. Mojtahedi, C. Wang, and V. W. Y. Tam, "Construction and demolition waste management contributing factors coupled with reduce, reuse, and recycle strategies for effective waste management: A review," *J. Clean. Prod.*, vol. 263, p. 121265, 2020, doi: <https://doi.org/10.1016/j.jclepro.2020.121265>.
- [6] A. Mistri, S. K. Bhattacharyya, N. Dharmi, A. Mukherjee, and S. V Barai, "A review on different treatment methods for enhancing the properties of recycled aggregates for sustainable construction materials," *Constr. Build. Mater.*, vol. 233, p. 117894, 2020, doi: <https://doi.org/10.1016/j.conbuildmat.2019.117894>.
- [7] P. Villoria-Sález, C. Porras-Amores, and M. del Río Merino, "2 - Estimation of construction and demolition waste," in *Advances in Construction and Demolition Waste Recycling*, F. Pacheco-Torgal, Y. Ding, F. Colangelo, R. Tuladhar, and A. Koutamanis, Eds. Woodhead Publishing, 2020, pp. 13–30.
- [8] G. Azúa, M. González, P. Arroyo, and Y. Kurama, "Recycled coarse aggregates from precast plant and building demolitions: Environmental and economic modeling through stochastic simulations," *J. Clean. Prod.*, vol. 210, pp. 1425–1434, 2019, doi: <https://doi.org/10.1016/j.jclepro.2018.11.049>.
- [9] S. Narahara *et al.*, "Evaluation of concrete made from recycled coarse aggregates by pulsed power discharge," in *2007 16th IEEE International Pulsed Power Conference*, Jun. 2007, vol. 1, pp. 748–751, doi: 10.1109/PPPS.2007.4651948.
- [10] N. N. Kencanawati, A. Akmaluddin, I. N. Merdana, N. Nuraida, I. R. Hadi, and M. Shigeishi, "Improving of Recycled Aggregate Quality by Thermal-mechanical-chemical Process," *Procedia Eng.*, vol. 171, pp. 640–644, 2017, doi: <https://doi.org/10.1016/j.proeng.2017.01.399>.
- [11] N. N. Kencanawati, J. Fajrin, B. Anshari, A. Akmaluddin, and M. Shigeishi, "Evaluation of High Grade Recycled Coarse Aggregate Concrete Quality Using Non-Destructive Testing Technique," *Appl. Mech. Mater.*, vol. 776, pp. 53–58, 2015, doi: 10.4028/www.scientific.net/AMM.776.53.
- [12] S. Kenai, "3 - Recycled aggregates," in *Waste and Supplementary Cementitious Materials in Concrete*, R. Siddique and P. Cachim, Eds. Woodhead Publishing, 2018, pp. 79–120.
- [13] W. Chen *et al.*, "Adopting recycled aggregates as sustainable construction materials: A review of the scientific literature," *Constr. Build. Mater.*, vol. 218, pp. 483–496, 2019, doi: <https://doi.org/10.1016/j.conbuildmat.2019.05.130>.
- [14] Y. Sui, C. Ou, S. Liu, J. Zhang, and Q. Tian, "Study on Properties of Waste Concrete Powder by Thermal Treatment and Application in Mortar," *Appl. Sci.*, vol. 10, no. 3, 2020, doi: 10.3390/app10030998.
- [15] Y. J. Kim and Y. W. Choi, "Utilization of waste concrete powder as a substitution material for cement," *Constr. Build. Mater.*, vol. 30, pp. 500–504, 2012, doi: <https://doi.org/10.1016/j.conbuildmat.2011.11.042>.
- [16] H. Kim, E. Ahn, S. Cho, M. Shin, and S.-H. Sim, "Comparative analysis of image binarization methods for crack identification in concrete structures," *Cem. Concr. Res.*, vol. 99, pp. 53–61, 2017.
- [17] X. Ma and Z. Wang, "Effect of Ground Waste Concrete Powder on Cement Properties," *Adv. Mater. Sci. Eng.*, vol. 2013, p. 918294, 2013, doi: 10.1155/2013/918294.
- [18] J. A. Purkiss, *Fire Safety Engineering Design of Structures*, Second. Elsevier, 2007.
- [19] P. K. Mehta and P. J. M. Monteiro, *Concrete: microstructure, properties, and materials*. McGraw-Hill Education, 2014.
- [20] SNI 03-6827-2002, "Indonesia National Standard Code: Testing Method for Initial Setting Time of Portland Cement using Vicat Tools for Civil Works," Jakarta, Indonesia, 2002.
- [21] SNI 1974:2011, "Cara uji kuat tekan beton dengan benda uji silinder," Jakarta, Indonesia.
- [22] SNI 03-1750-1990, "Indonesian National Standard: Aggregate for Concrete, Quality and Testing Methods," Jakarta, Indonesia, 1990.



Recycled Powder Concrete

ORIGINALITY REPORT

7%

SIMILARITY INDEX

6%

INTERNET SOURCES

4%

PUBLICATIONS

1%

STUDENT PAPERS

PRIMARY SOURCES

1

dx.doi.org

Internet Source

1%

2

Irpan Hidayat, Alice Siauwantara. "The Value Compressive Strength and Split Tensile Strength on Concrete Mixture With Expanded Polystyrene Coated by Surfactant Span 80 as a Partial Substitution of Fine Aggregate", EPJ Web of Conferences, 2014

Publication

1%

3

www.jurnal.unsyiah.ac.id

Internet Source

1%

4

"Proceedings of the 2nd International Conference on Experimental and Computational Mechanics in Engineering", Springer Science and Business Media LLC, 2021

Publication

1%

5

d-nb.info

Internet Source

1%

6	Felix F. Udoeyo, Philibus U. Dashibil. "Sawdust Ash as Concrete Material", Journal of Materials in Civil Engineering, 2002 Publication	1 %
7	www.mdpi.com Internet Source	1 %
8	Buan Anshari, Wayan Sugiarta, Fathmah Mahmud, Aryani Rofaida, Pathurrahman. "Experimental study on the strength of double shear timber connection using bamboo dowel fastener", AIP Publishing, 2017 Publication	1 %
9	eprints.uty.ac.id Internet Source	1 %
10	mafiadoc.com Internet Source	1 %

Exclude quotes On

Exclude matches < 1%

Exclude bibliography On

Recycled Powder Concrete

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7

PAGE 8

PAGE 9

PAGE 10
