



Green Materials and Technology

International Symposium on Green Materials
and Technology (ISGMT)

Edited by
Dr. Subaer

 TRANS TECH PUBLICATIONS

Paper Titles

The Effects of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ Ratios on the Volumetric Properties of Fly Ash Geopolymer Artificial Aggregates

359



Abstract:

This study was conducted as a part of a research to assess the influence of the volumetric properties of geopolymer artificial aggregates made of fly ash to the performance of asphalt mixture to be used in pavement layers. This paper presents the parameters adopted during the production of geopolymer artificial aggregates which may affect the volumetric properties and the structure of the aggregates. The investigated volumetric properties included specific gravity and water absorption. In the experiment laboratory, two variables were utilized for producing the artificial aggregates, which might affect the considered volumetric properties. Those variables are pan-granulator slopes and alkaline ratios (the ratios of Sodium Silicate to Sodium Hydroxide). The pan-granulator slopes were set at 3 different angles, i.e. 45° , 50° , and 55° . The selected alkaline ratios were 1.5, 2.0, 2.5, and 3.0. The test results indicated that the best volumetric properties were obtained at a slope of 50° and alkaline ratio of 2.5. The bulk specific gravity values at the best volumetric properties were found to be: 1) oven dry at 1.9 grams/cm^3 ; 2) saturated surface dry (SSD) at 2.0 grams/cm^3 , and 3) apparent at 2.1 grams/cm^3 with 6% water absorption. In addition, the interfacial transition zone and microstructure aggregates were examined by using Scanning Electron Microscope (SEM). In this study, it was found that there were effects of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ ratios and the granulation method on the volumetric properties.

[Access through your institution](#)

ADD TO CART

Info:

Periodical:	Materials Science Forum (Volume 967)
Pages:	228-235
DOI:	https://doi.org/10.4028/www.scientific.net/MSF.967.228
Citation:	Cite this paper
Online since:	August 2019
Authors:	I Dewa Made Alit Karyawan , Januarti Jaya Ekaputri , Iswandaru Widyatmoko , Ervina Ariatedja*
Keywords:	Artificial Aggregate , Fly Ash , Geopolymer , Granulation , Volumetric Properties
Export:	RIS , BibTeX
Price:	39,00 €
Permissions:	Request Permissions
Share:	

* - Corresponding Author

References

Cited by

Related Articles

DISTRIBUTION & ACCESS
FOR PUBLICATION
INSIGHTS

[DOWNLOADS](#)

[ABOUT US](#)

[POLICY & ETHICS](#)

[CONTACT US](#)

[IMPRINT](#)

[PRIVACY POLICY](#)

[SITEMAP](#)

[ALL CONFERENCES](#)

[ALL SPECIAL ISSUES](#)

[ALL NEWS](#)

Scientific.Net is a registered brand of Trans Tech Publications Ltd
© 2023 by Trans Tech Publications Ltd. All Rights Reserved

Search

Volumes

Materials Science Forum Vol. 967

DOI: <https://doi.org/10.4028/www.scientific.net/MSF.967>

ToC: [Table of Contents](#)

Search

< 1 2 3 **4** 5 >

Paper Title Page

Properties of Alkali Activated Slag Concrete Incorporating Waste Materials as Aggregate: A Review 214

Authors: Adeyemi Adesina

Abstract: Alkali activated slag (AAS) has gained huge attention in recent years due to its ability to replace ordinary Portland cement (OPC) as a [...more](#)

Durability Enhancement of Concrete Using Nanomaterials: An Overview 221

Authors: Adeyemi Adesina

Abstract: Different initiatives have evolved over the years to improve the durability of concrete, and one of the promising areas gaining attention [...more](#)

The Effects of Na₂SiO₃/NaOH Ratios on the Volumetric Properties of Fly Ash Geopolymer Artificial Aggregates

228

Authors: I Dewa Made Alit Karyawan, Januarti Jaya Ekaputri, Iswandaru Widyatmoko, Ervina Ariatedja

Abstract: This study was conducted as a part of a research to assess the influence of the volumetric properties of geopolymer artificial aggregates

[...more](#)

A Review on Heat Released in early Geopolymerization by Calorimetric Study

236

Authors: Rosnita Mohamed, Rafiza Abd Razak, Mohd Mustafa Al Bakri Abdullah

Abstract: An exothermic chemical reaction between cement and water or is called as hydration of cement produced heat in which gives

[...more](#)

Improvement of Kaolin Based Geopolymer Coated Wood Substrates for Use in NaOH Molarity

241

Authors: Ramasamy Shamala, Mohd Mustafa Al Bakri Abdullah, Hussin Kamarudin, Huang Yue, Wang Jin

Abstract: Geopolymer system which has high demand, especially among carbon conscious end users resulted in various research works on

[...more](#)

Performance of Undershot Waterwheel Curved Blade of the Laboratory Scale

250

Authors: Irwan Lie Keng Wong, Atus Buku, Josefine Ernestine Latupeirissa, Herby Calvin Pascal Tiwouy

Abstract: Undershot waterwheels have been used by the people in rural areas to lift and distribute the water to the bottom which is higher than

[...more](#)

Synthesis and Characterization of Nanopraticle Hematite (α -Fe₂O₃) Minerals from Natural Iron Sand Using Co-Precipitation Method and its Potential Applications as Extrinsic Semiconductor Materials Type-N

259

Authors: Muhammad Rizal Fahlepy, Yuyu Wahyuni, Muhamma Andhika, Arini Tiwow Vistarani, Subaer Subaer

Abstract: This research is about nanoparticles hematite (NPH) synthesized and characterized from natural iron sands using co-

[...more](#)

**Thermo-Mechanical Properties of Geopolymer/Carbon
Fiber/TiO₂ Nanoparticles (NPs) Composite**

267

Authors: Subaer Subaer, Abdul Haris, Noor Afifah Kharisma, Nur Akifah, Risna Zulwiyati

Abstract: The main objective of this study is to investigate the thermo-mechanical properties of composite made from geopolymer/carbon

[...more](#)

**Development of Photoactive Nano TiO₂ Thin Film-Geopolymer
Based on Laterite Soils Deposit Gowa Regency as Self-Cleaning
Material**

274

Authors: Anita Dewi Permatasari, Nursalfaul Fahira, Nurul Husna Muslimin, Subaer Subaer

Abstract: The main objectives of this study is to investigate the properties of photoactive Nano TiO₂ thin film-geopolymer based on laterite soils

[...more](#)

**The Properties of Geopolymer-Cuo Nanoparticles as a
Functional Composite**

281

Authors: Annisa Nur Qadry, Noor Afifah Kharisma, Subaer Subaer

Abstract: CuO nanoparticles (CuO-NPs) have been attracted much attention recently as a functional material. This study was conducted to

[...more](#)

Showing 31 to 40 of 42 Paper Titles



DISTRIBUTION & ACCESS

FOR PUBLICATION

INSIGHTS

DOWNLOADS

ABOUT US

POLICY & ETHICS

CONTACT US

[IMPRINT](#)

[PRIVACY POLICY](#)

[SITEMAP](#)

[ALL CONFERENCES](#)

[ALL SPECIAL ISSUES](#)

[ALL NEWS](#)

Scientific.Net is a registered brand of Trans Tech Publications Ltd
© 2023 by Trans Tech Publications Ltd. All Rights Reserved

Green Materials and Technology

International Symposium on Green Materials and Technology (ISGMT)

Selected, peer reviewed papers from the
1st International Symposium on
Green Materials and Technology (1st ISGMT),
September 29 – 30, 2018, Makassar, Indonesia

Edited by

Dr. Subaer

The Effects of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ Ratios on the Volumetric Properties of Fly Ash Geopolymer Artificial Aggregates

I DEWA Made Alit Karyawan^{12a}, JANUARTI Jaya Ekaputri^{1b}, ISWANDARU Widyatmoko^{3c},
ERVINA Ahyudanari^{1d*}

¹Departemen of Civil Engineering, Faculty of Civil, Environmental, and Earth Engineering,
Institut Teknologi Sepuluh Nopember
Kampus ITS Sukolilo, Surabaya 60111, East Java-Indonesia

²Departemen of Civil Engineering, Faculty of Engineering, Universitas Mataram
Jalan Majapahit 62 Mataram 83125, Nusa Tenggara Barat-Indonesia

³Transportation and Infrastructure Materials Research, AECOM
12 Regan Way, Nottingham NG9 6RZ, United Kingdom

^adewaalit@unram.ac.id, ^bjanuarti@ce.its.ac.id, ^cdaru.widyatmoko@aecom.com,
^dervina@ce.its.ac.id

Keyword: artificial aggregates, geopolymer, fly ash, volumetric properties, granulation

Abstract This study was conducted as a part of a research to assess the influence of the volumetric properties of geopolymer artificial aggregates made of fly ash to the performance of asphalt mixture to be used in pavement layers. This paper presents the parameters adopted during the production of geopolymer artificial aggregates which may affect the volumetric properties and the structure of the aggregates. The investigated volumetric properties included specific gravity and water absorption. In the experiment laboratory, two variables were utilized for producing the artificial aggregates, which might affect the considered volumetric properties. Those variables are pan-granulator slopes and alkaline ratios (the ratios of Sodium Silicate to Sodium Hydroxide). The pan-granulator slopes were set at 3 different angles, i.e. 45° , 50° , and 55° . The selected alkaline ratios were 1.5, 2.0, 2.5, and 3.0. The test results indicated that the best volumetric properties were obtained at a slope of 50° and alkaline ratio of 2.5. The bulk specific gravity values at the best volumetric properties were found to be: 1) oven dry at 1.9 grams/cm^3 ; 2) saturated surface dry (SSD) at 2.0 grams/cm^3 , and 3) apparent at 2.1 grams/cm^3 with 6% water absorption. In addition, the interfacial transition zone and microstructure aggregates were examined by using Scanning Electron Microscope (SEM). In this study, it was found that there were effects of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ ratios and the granulation method on the volumetric properties.

Introduction

The increasing of infrastructure development has caused an increase in aggregate demand. Aggregates are the main ingredients for concretes, both portland cement concrete and asphalt concrete. Aggregates are produced by crushing natural rocks into smaller sizes, according to the required sizes, in gradations. Therefore, natural rock explorations are carried out to supply the required aggregates in the infrastructure industry which causes the resource to decrease [1]. As an illustration, to make a mixture of asphalt concrete, 90%-95% of the aggregates from the mixture weight is used which is equal to 75%-85% of the mixture volume [2]. The efforts to fulfill this aggregate needs include creating artificial aggregates. One of them is by using fly ash geopolymer [3][4]. Fly ash geopolymers have higher mechanical strength, temperature resistance, and durability in comparison with cement. Due to this nature, fly ash geopolymers gain more attention and interest from researchers. An investigation on the fly ash geopolymer durability with metakaolin at high temperatures and acids conclude that geopolymers have better durability compared to Portland cement under the same conditions [5].

*corresponding author

Artificial aggregates, used for construction, must have several properties to comply with the requirements. Therefore, to be used as an asphalt concrete mixture, these properties must be identified through testing. These properties include specific gravity and absorption [6]. Geopolymer aggregates based on fly ash holds the potential to be utilized as artificial aggregate materials because their quality can be improved in the mixing process [1]. The process of making aggregates with fly ash materials includes making pellets through a sintering process by heating the materials above 1,000°C [7] and through pellet making by cold bonding methods [3][7]. Geopolymerization is highly dependent on the fly ash's physicochemical properties and on the availability of silicate solutions and aluminate. In this case, an additional concentration of sodium hydroxide, capable of increasing the amount of silicate and aluminate, can be dissolved in the mixture. Therefore, the ratio of alkali activators plays a crucial role in the geopolymerization process [4].

This paper is a part of a study on the manufacture of geopolymer aggregates made from fly ash and alkali activators. This paper only explained specific gravity properties and aggregate absorption. The emphasis was on the effects of pan granulator slopes and the alkali activator ratios on the volumetric properties of artificial aggregates. This resulted in a part of the research to get aggregate with the properties that complies the requirements to be utilized as a mixture of asphalt concrete.

Experiment

The mixture material was fly ash taken from Suralaya Steam Power Plant unit 1-4, Indonesia. The chemical content of fly ash based on the XRF test is indicated in Table 1. The main difference between class F fly ash and class C fly ash is that the latter contains a higher amount of calcium [8]. Fly ash is classified as class C when the CaO content is more than 10% and the amount of SiO₂, Al₂O₃, and Fe₂O₃ is more than 50%. The proportion of fly ash in geopolymer paste was 75%, while the alkali activator amounted to 25%. The basic activator contained 8M of Sodium Silicate (Na₂SiO₃) and Sodium Hydroxide (NaOH). The aggregates were made through cold mixing process with granulation system using a granulator. The materials for making artificial aggregate are presented in Figure 1.

Table 1 Chemical composition of fly ash based on XRF test results

No	Compound	Content (%)	No	Compound	Content (%)
1	MgO	0.20	9	MnO	0.35
2	Al ₂ O ₃	18.05	10	Fe ₂ O ₃	18.45
3	SiO ₂	45.00	11	CuO	0.04
4	K ₂ O	1.47	12	ZnO	0.05
5	CaO	10.85	13	MoO ₃	3.29
6	TiO ₂	1.70	14	BaO	0.27
7	V ₂ O ₅	0.07	15	Re ₂ O ₇	0.25
8	Cr ₂ O ₃	0.03	16	Na ₂ O	-

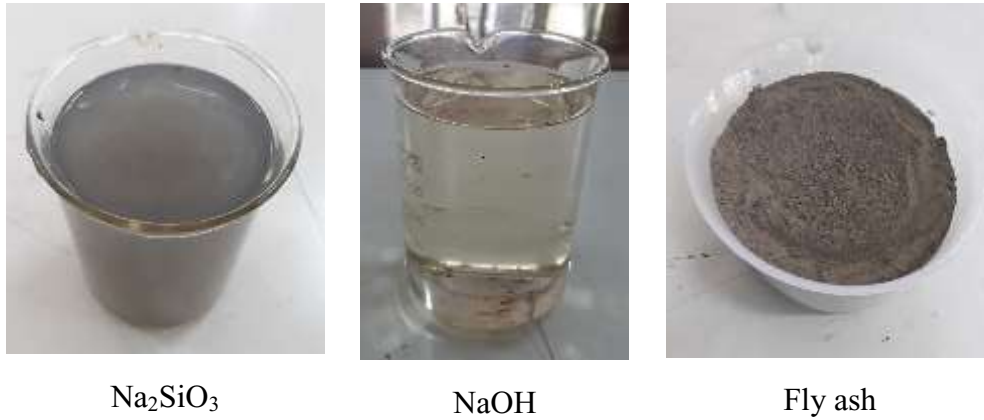


Fig 1. Materials for making aggregates

The pan granulator slopes were altered by adjusting the screw on the back of the pan as seen in Figure 2. The properties of aggregates as a mixture of asphalt concrete include specific gravity, absorption, hardness, adhesion to asphalt, durability, and impact. Nevertheless, this paper only discussed the volumetric properties, i.e. specific gravity and absorption. Specific gravity consists of bulk, apparent, and effective specific gravity. Specific gravity depends on the element and the porosity of the aggregate particles which can be defined as follows: a) all of the pore spaces (bulk specific gravity); b) some of the pore spaces (effective specific gravity); c) none of the pore spaces (apparent specific gravity) [9]. The absorption was in comparison with the change in the aggregate mass because of the presence of water absorbed in the pore space in constituent particles with dry conditions [10].



Fig 2. Granulator and pan slope

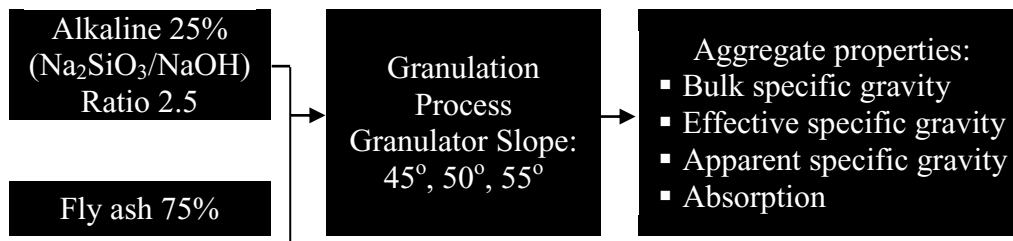


Fig 3. Experiment to find the best slope [11]

The influential parameters in the process of making pellets included (i) rotation speed of pelletizer discs; (ii) angle of pelletizer disc; (iii) content moisture; and (iv) pelletization duration [12]. To determine the effects of the slopes on volumetric properties, 3 slope degrees were trialed, i.e. 45°, 50°, and 55° with an alkali activator ratio of 2.5 [11]. The best properties produced from these 3 slopes were then selected. The slope that produced the best properties were utilized in an attempt to create aggregates with activator ratios of 1.5, 2.0, 2.5 and 3.0. From the experiment, the best angle and ratio were identified to obtain the best volumetric properties.

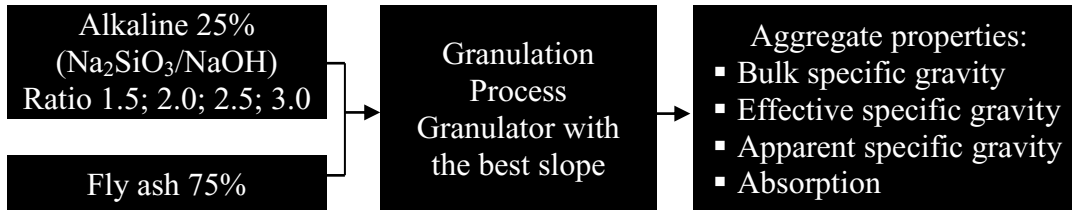


Fig 4. Experiment to find the best alkaline ratio

All test of artificial aggregates were carried out in the laboratory of Institut Teknologi Sepuluh Nopember, Surabaya. The aggregates were tested after 28 days [13]. The properties of volumetric aggregates, i.e. specific gravity and absorption, were tested at the Laboratory of Transportation and Road Materials of Institut Teknologi Sepuluh Nopember. The XRF testing was conducted to determine the chemical composition of fly ash [4]. Furthermore, SEM test was performed on the best artificial aggregates from the property test analysis results. The SEM test results were employed to determine the density of the matrix and fly ash reaction [4]. XRF and SEM tests were conducted at the Energy Laboratory of Institut Teknologi Sepuluh Nopember.

Results and Discussion

Aggregate properties based on pan granulator slope variations

The aggregates made with a ratio of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ of 2.5 and slopes of 45°, 50° and 55° are shown in Figure 5 as well as the test results of volumetric property value based on pan granulator slopes. The aggregates were made by setting the ratio of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ at the value of 2.5. In the picture, it is evident that specific gravity did not indicate a linear correlation. On the other hand, in general, 50° slope had the lowest value, except for the apparent specific gravity. The Normal Bulk Specific Gravity of 2.4 to 2.9 was set for natural aggregates [14]. The results obtained from 3 slopes did not correlate with the natural aggregates.

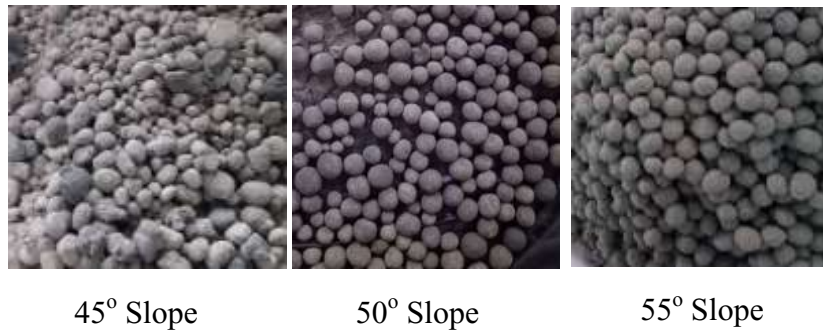


Fig 5. Artificial aggregates with $\text{Na}_2\text{SiO}_3/\text{NaOH}$ ratio of 2.5 and slope variations [11]

In Figure 6 on absorption values, it was indicated that the smallest value was obtained at 50° slope. The absorption requirement to be asphalt mixture was 3% at most. Because all absorption values obtained were less than 3%, the best value was obtained at the slope angle of 50°. The granulation process speed affected the specific gravity and absorption [12]. In Figure 6, it is evident that slopes did not correlate with the absorption level.

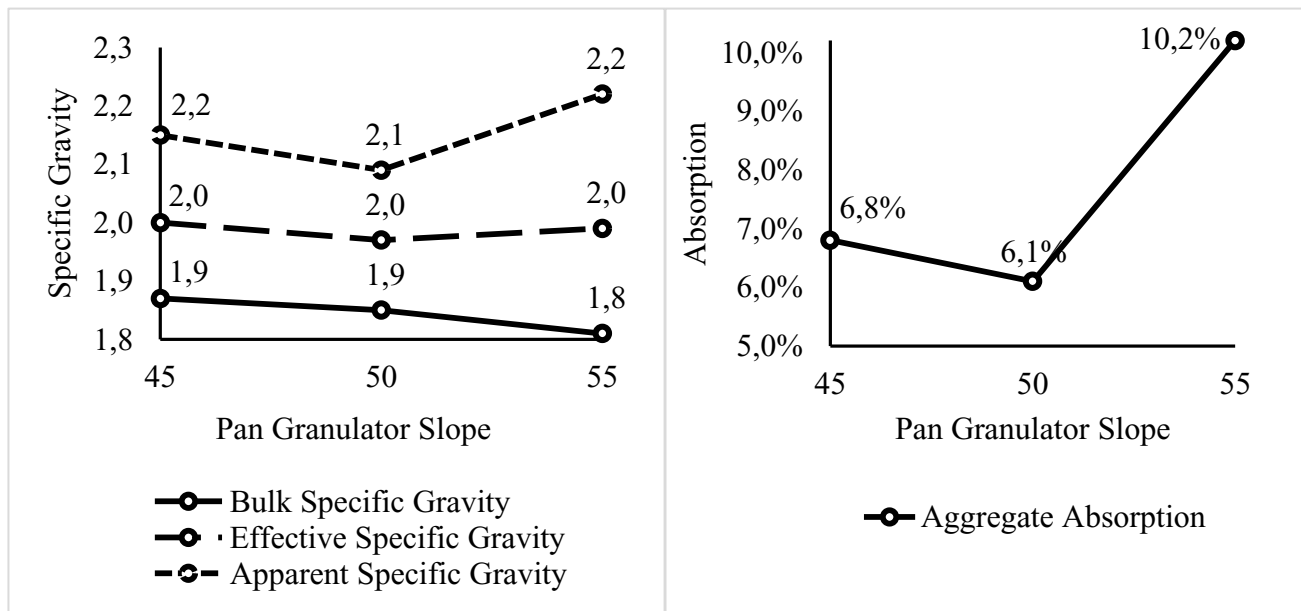


Fig 6. The correlation between pan granulator slopes and specific gravity and absorption [11]

Aggregate properties based on alkaline ratio variations

Based on the test results in Figure 6, to get the properties based on variations in the ratios of $\text{Na}_2\text{SiO}_3/\text{NaOH}$, the pan granulator slope was set at 50°. Figure 7 displayed the aggregates made with 50° slope and variations in the ratios of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ of 1.5, 2.0, 2.5 and 3.0. The test results in Figure 8 suggested the value of volumetric properties based on pan granulator slopes. In the figure, it can be seen that specific gravity had the same trend on the effective specific gravity and apparent specific gravity. However, ratio 2.5 suggested a different tendency for bulk specific gravity. The results indicated that a high ratio did not necessarily produce a high value or vice versa. The normal bulk specific gravity were 2.4 to 2.9 for natural aggregates [14]. The results obtained from the 3 ratios indicated that the properties of artificial aggregates did not correlate with the natural aggregates.

There was an effect of alkaline ratios on the compressive strength of geopolymer paste [15][16]. In related research about the correlation of compressive strength and the ratio of $\text{Na}_2\text{SiO}_3/\text{NaOH}$, the ratios of 0.5, 1, 1.5, 2, and 2.5 were utilized. It was found that the optimum ratio of 2 and 2.5 resulted in the highest compressive strength of 2.86 MPa [17][18]. Therefore, to obtain good aggregate properties, the alkali activator needs to be modified. Such a modification can be made on the use of alkali activator/fly ash ratio, $\text{Na}_2\text{SiO}_3/\text{NaOH}$ ratio, and NaOH molarity. Therefore, a trial must first be conducted to obtain good properties. Higher compressive strength will produce better aggregate properties [1].



Fig 7. Artificial aggregates with a slope of 50° and variations in the ratios of $\text{Na}_2\text{SiO}_3/\text{NaOH}$

In Figure 8, at a ratio of 2.5, the smallest absorption values were obtained. To obtain the maximum absorption requirements of 3% to make asphalt mixture, the best value was obtained at an alkali ratio of 2.5 [11].


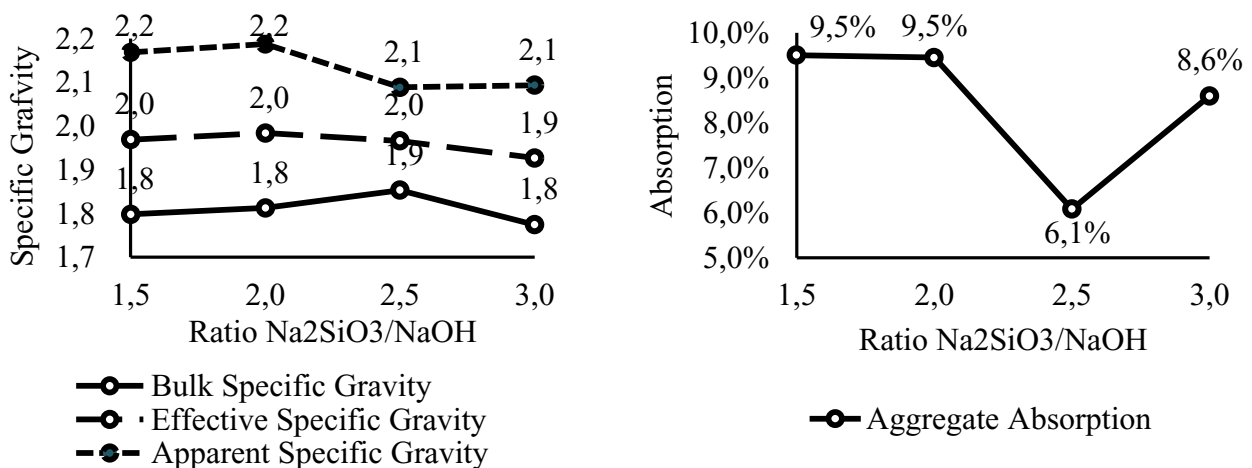



Figure 8. The correlation between specific gravity and absorption with Na_2SiO_3 and NaOH ratios

Based on the obtained results, artificial aggregates did not meet the requirements as asphalt mixture. However, from these results, the best aggregates were obtained at 2.5 ratio of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ with 8M NaOH and 50° slope [11]


In Figure 9, the fly ash morphology characterization analysis with SEM indicated fly ash microstructure with various features of size, shapes, and surface. The particles were mostly spherical called as cenospheres[19]. On the other hand, the artificial aggregates suggested that in this proportion, good solidification on the fly ash granules with alkaline activators took place. In addition, there was a geopolymerization reaction between fly ash and alkali. This was evident where most of the fly ash particles were dissolved by the alkaline activator. Only a few reacted irregularly or partially [13].

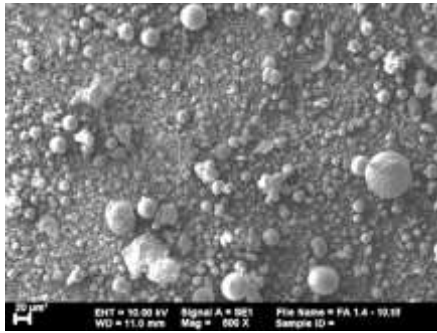


Fly ash (500X)

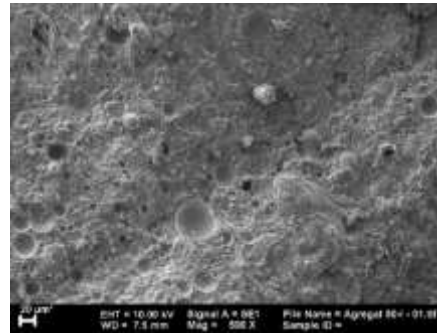

Artificial Aggregates (500X)

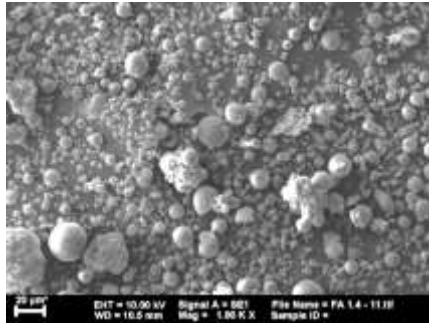

Fly ash (1,000X)

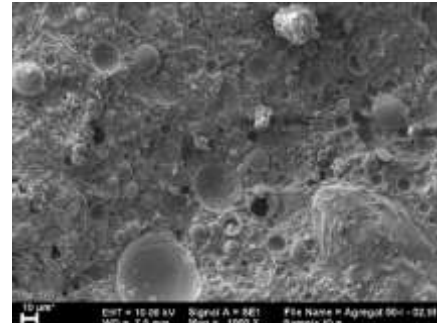

Artificial Aggregates (1,000X)

Fig 9. Morphology of fly ash and artificial aggregates with 50° slope and 2.5 ratio

Summary

- The aggregate properties varied for each difference in the alkaline ratio ($\text{Na}_2\text{SiO}_3/\text{NaOH}$). The difference in the ratio of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ was not directly proportional to the specific gravity of the aggregates. The same phenomenon occurred for absorption where it had no correlation with the increase in the alkaline ratio. The smallest absorption took place at the ratio of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ of 2.5.
- Two variables were employed in this study, namely the granulator slopes and the alkali ratios. The results indicated that both variables caused effects on aggregate volumetric properties. However, these effects had no linear correlations, meaning that a high tilt angle did not necessarily increase the volumetric properties or vice versa. The same correlation also applied for the alkaline ratios.

Acknowledgments

The authors would like to express their utmost gratitude and acknowledgment to those who contributed directly or indirectly to this project. Special gratitude is extended to Beasiswa Unggulan Dosen Indonesia-Dalam Negeri (BUDI-DN), through Lembaga Pengelola Dana Pendidikan (LPDP) of the Ministry of Finance of the Republic of Indonesia for their support through the Indonesian education scholarship program. Additional appreciation is to Hilda Yuliana who sponsored by EPI-UNET (Eastern Part of Indonesia University Network) research grant for supporting part of data in this article.

References

- [1] I. D. M. A. Karyawan, E. Ahyudanari, and J. J. Ekaputri, "Potential Use of Fly Ash Base-Geopolymer as Aggregate Substitution in Asphalt Concrete Mixtures," *Int. J. Eng. Technol.*, vol. 9, no. 5, pp. 3744–3752, 2017.
- [2] P. B. Cachim, "Mechanical properties of brick aggregate concrete," *Constr. Build. Mater.*, 2009.
- [3] J. Thomas, "Concrete made using cold bonded artificial aggregate," *Am. J. Eng. Res.*, no. 1, pp. 2320–847, 2013.
- [4] H. Fansuri, D. Prasetyoko, Z. Zhang, and D. Zhang, "The effect of sodium silicate and sodium hydroxide on the strength of aggregates made from coal fly ash using the geopolymerisation method," *Asia-Pacific J. Chem. Eng.*, 2012.
- [5] P. Duan, C. Yan, W. Zhou, and D. Ren, "Fresh properties, compressive strength and microstructure of fly ash geopolymer paste blended with iron ore tailing under thermal cycle," *Constr. Build. Mater.*, 2016.
- [6] E. Ahyudanari, J. J. Ekaputri, and M. Tardas, "Analysis of Coal Waste Solidification as an Alternative Filler Material in Asphalt Concrete Mixture," *Mater. Sci. Forum*, vol. 841, no. November 2015, pp. 65–71, 2016.
- [7] P. Gomathi and A. Sivakumar, "Characterization on the strength properties of pelletized fly ash aggregate," *ARPN J. Eng. Appl. Sci.*, vol. 7, no. 11, pp. 1523–1532, 2012.
- [8] X. Li, X. Ma, S. Zhang, and E. Zheng, "Mechanical Properties and Microstructure of Class C Fly Ash-Based Geopolymer Paste and Mortar," pp. 1485–1495, 2013.
- [9] B. Arumugam, "Effect of Specific Gravity on Aggregate Varies the Weight Of Concrete Cube," *SSRG Int. J. Civ. Eng.*, vol. 1, no. August, pp. 1–9, 2014.
- [10] ASTM C127 - 15, *Standard Test Method for Relative Density (Specific Gravity) and Absorption of Coarse Aggregate*.
- [11] H. Yuliana, I. D. M. A. Karyawan, S. Murtiadi, J.J. Ekaputri, and E. Ahyudanari, "The Effect of Slope Granulator on The Characteristic of Artificial Geopolymer Aggregate," *J. Eng. Sci. Technol.*, vol. 14, issue 3, June 2019. (accepted for publication, Dec 3, 2018)
- [12] K. I. Harikrishnan and K. Ramamurthy, "Influence of pelletization process on the properties of fly ash aggregates," *Waste Manag.*, vol. 26, no. 8, pp. 846–852, Jan. 2006.
- [13] M. Z. N. Khan, F. uddin A. Shaikh, Y. Hao, and H. Hao, "Synthesis of high strength ambient cured geopolymer composite by using low calcium fly ash," *Constr. Build. Mater.*, 2016.
- [14] G. B. Singh, "Artificial Aggregate Production from Fly Ash," *Masterbuilder Bur.*, 2016.
- [15] A. M. Mustafa Al Bakri, H. Kamarudin, M. Bnhussain, A. R. Rafiza, and Y. Zarina, "Effect of Na₂SiO₃/NaOH ratios and NaOH molarities on compressive strength of fly-ash-based geopolymer," *ACI Mater. J.*, vol. 109, no. 5, pp. 503–508, 2012.
- [16] A. V. Lăzărescu, H. Szilagyi, C. Baeră, and A. Ioani, "The Effect of Alkaline Activator Ratio on the Compressive Strength of Fly Ash-Based Geopolymer Paste," *IOP Conf. Ser. Mater. Sci. Eng.*, vol. 209, no. 1, 2017.
- [17] P. Risdanareni, J. J. Ekaputri, and M. M. A. B. Abdullah, "Effect of Alkaline Activator Ratio to Mechanical Properties of Geopolymer Concrete with Trass as Filler," *Appl. Mech. Mater.*, vol. 754–755, no. April, pp. 406–412, 2015.
- [18] P. Risdanareni and J. J. Ekaputri, "The Influence of Alkali Activator Concentration to Mechanical Properties of Geopolymer Concrete with Trass as a Filler," *Mater. Sci. Forum*, vol. 803, pp. 125–134, 2015.
- [19] Y. Tajunnisa, M. Sugimoto, T. Sato, J. J. Ekaputri, and M. Shigeishi, "Characterization of Low Calcium Fly," 2016, no. May.



Source details

Materials Science Forum

Scopus coverage years: from 1984 to 1986, from 1994 to 2022

Publisher: Trans Tech Publications Ltd

ISSN: 0255-5476 E-ISSN: 1662-9752

Subject area: Engineering: Mechanical Engineering Materials Science: General Materials Science

Engineering: Mechanics of Materials Physics and Astronomy: Condensed Matter Physics

Source type: Book Series

CiteScore 2021

0.9



SJR 2021

0.211



SNIP 2021

0.338



[View all documents >](#)

[Set document alert](#)

[Save to source list](#) [Source Homepage](#)

[CiteScore](#) [CiteScore rank & trend](#) [Scopus content coverage](#)

i Improved CiteScore methodology



CiteScore 2021 counts the citations received in 2018-2021 to articles, reviews, conference papers, book chapters and data papers published in 2018-2021, and divides this by the number of publications published in 2018-2021. [Learn more >](#)

CiteScore 2021

$$0.9 = \frac{6,825 \text{ Citations } 2018 - 2021}{7,354 \text{ Documents } 2018 - 2021}$$

Calculated on 05 May, 2022

CiteScoreTracker 2022

$$1.0 = \frac{5,890 \text{ Citations to date}}{6,048 \text{ Documents to date}}$$

Last updated on 05 April, 2023 • Updated monthly

CiteScore rank 2021

Category	Rank	Percentile
Engineering		
Mechanical Engineering	#478/601	20th
Materials Science		
General Materials Science	#375/455	17th
Engineering		

[View CiteScore methodology >](#) [CiteScore FAQ >](#) [Add CiteScore to your site](#)

About Scopus

[What is Scopus](#)

[Content coverage](#)

[Scopus blog](#)

[Scopus API](#)

[Privacy matters](#)

Language

[日本語版を表示する](#)

[查看简体中文版本](#)

[查看繁體中文版本](#)

[Просмотр версии на русском языке](#)

Customer Service

[Help](#)

[Tutorials](#)

[Contact us](#)

ELSEVIER

[Terms and conditions](#) ↗ [Privacy policy](#) ↗

Copyright © Elsevier B.V. ↗. All rights reserved. Scopus® is a registered trademark of Elsevier B.V.

We use cookies to help provide and enhance our service and tailor content. By continuing, you agree to the use of cookies ↗.

