

2021_IOP__Tri_Wettability_Seng on_Scopus_Q4.pdf

by

Submission date: 15-Jun-2023 10:08PM (UTC-0500)

Submission ID: 2117035002

File name: 2021_IOP__Tri_Wettability_Sengon_Scopus_Q4.pdf (440.99K)

Word count: 3277

Character count: 16841

PAPER · OPEN ACCESS

5

Wettability and Treatability of Sengon (*Paraserianthes falcataria* (L.) I.C. Nielsen) wood from NTB

9

To cite this article: A T Lestari *et al* 2021 *IOP Conf. Ser.: Earth Environ. Sci.* **891** 012015

View the [article online](#) for updates and enhancements.



The Electrochemical Society
Advancing solid state & electrochemical science & technology

241st ECS Meeting

May 29 – June 2, 2022 Vancouver • BC • Canada

Extended abstract submission deadline: Dec 17, 2021

Connect. Engage. Champion. Empower. Accelerate.
Move science forward



Submit your abstract



5 Wettability and Treatability of Sengon (*Paraserianthes falcataria* (L.) I.C. Nielsen) wood from NTB

A T Lestari¹, E Wahyuningsih¹, M Syaputra¹, H Anwar¹, P K Suparyana²
and F N Ritonga³

¹ Department of Agribusiness, Faculty of Agriculture, University of Mataram,
Jl. Pendidikan No.37, Kota Mataram 83115, Indonesia

² Department of Agribusiness, Faculty of Agriculture, University of Mataram,
Jl. Pendidikan No.37, Kota Mataram 83115, Indonesia

³ State Key Laboratory of Tree Genetics and Breeding, Forestry College, Northeast
Forestry University, Harbin 150040, China

E-mail: atlestari@unram.ac.id

ORCID ID: 0003-1587-8097

Abstract. The supply of wood from natural forests is decreasing as a result of the imbalance between harvesting and planting. The lack of wood supply from natural forests has resulted in relatively expensive wood prices. This can be anticipated by using fast-growing wood species. One type of fast-growing wood which is very abundantly available in NTB is sengon wood (*Paraserianthes falcataria* (L.) I.C. Nielsen). However, sengon wood has low durability so it is easily attacked by wood-destroying organisms. This condition can be overcome by making efforts to prevent wood damage in the form of preservation. This study aims to determine the wettability and treatability properties of sengon wood. The results of this study are expected to be basic information to improve the quality of sengon wood. The wettability test was carried out by measuring the contact angle between the liquid and the sample surface using the sessile drop method and the wood durability testing was carried out by measuring the retention and penetration of preservatives. The treatability test was carried out by measuring the absorption, retention, and penetration of preservatives. The results showed that the wettability of sengon is high with an equilibrium contact angle (θ_e) of 16.88 in the radial section and 12.51 in the tangential section. This shows that sengon wood has a good adhesion system for preservation. Treatability of sengon wood showed that the average retention and penetration are 10,21 kg/m³ and 7,33 mm. Based on the results of these measurements, sengon wood has met SNI 03-5010.1-1999 (wood preservation for housing and buildings).

1. Introduction

The supply of wood from natural forests is decreasing as a result of the imbalance between harvesting and planting [1]. The lack of wood supply from natural forests has resulted in relatively expensive wood prices [5]. The limited of long rotation wood can be overcome by utilizing fast-growing species like sengon wood (*Paraserianthes falcataria* (L.) I.C. Nielsen). Sengon wood is a species that is widely developed in



21
community forests in West Nusa Tenggara (NTB) Province [3]. The price of sengon wood in NTB using methods of stumpage price, market price, and social price also shows that sengon wood can be an alternative to wood from natural forests [4].

2
Fast-growing wood species are already in demand for use in the light-frame structural, woodworking, and wood composite board industries as the main source of raw material and are becoming leading wood product exports [5]. However, fast-growing wood species has low durability, so it is easily attacked by wood-destroying organisms (e.g. insects, fungi, bacteria, and marine borer) [6]. Since fast-growing wood species are often of inferior quality (e.g. low density, low dimensional stability, low durability, etc.), many modification techniques are used to improve wood properties such as heat treatment [7] and applying a coating layer [8]. One of the most common treatments is the application of preservatives [9].

1
The success of wood preservation can be influenced by the wettability and treatability of the wood. Wettability is the ability of a material to absorb liquid and provides information on the interaction between the wood surface and the liquid [7, 10, 11]. Wettability is influenced by various factors, such as wood species, wood density, type of liquid, surface roughness, and defects [12-16]. The wettability of wood can be obtained by measuring the contact angle between the liquid and the wood surface. A contact angle less than 90° indicates a high wettability where the liquid wets the surface well. A contact angle greater than 90° indicates low wettability where the liquid does not wet the surface well [17]. Thus, it is known that the higher the contact angle of a liquid, the lower its wettability. The characteristic is related to surface properties and affects the absorbency, adhesion, and finishing attributes of wood [18]. These characteristics also related to the treatability of the wood. The treatability of wood is influenced by its porous structure, wood moisture content, drying technique, preservative formulation, and treatment process [19].

Previous research has shown that fast-growing wood species can be used as a substitute for long-rotation wood by preservation. One indicator of the success of preservation is wettability. This study aims to determine the wettability and treatability properties of sengon wood. The results of this study are expected to be basic information to improve the quality of sengon wood. Wood quality improvement is expected to increase the resistance of wood to destroying organisms, thereby increasing the service life of the wood.

2. Materials and Methods

2.1. Wettability measurements

The samples used were radial and tangential section of sengon, made following the ASTM D 358-98 standard which requires the wood used to be free from defects [20]. The defect-free samples were cut into 3 radial section and 3 tangential section in dimension of 20 x 10 x 2 cm (longitudinal x tangential x radial). The samples were then conditioned at temperature of 21 °C until reached the final moisture content of 12-15%. The samples that have the appropriate size and water content were then sanded with sandpaper number 150.

The wettability test was carried out by measuring the contact angles between the water. Water choose to determine the wettability since water-based preservatives are the most widely used preservatives with various types in the world [21]. The contact angles between the water and the surface of the samples by the sessile drop method. The liquid with volume 0.2 ml was dropped using a dropper at 5 different points with a diagonal direction on each sample. The drop shapes on the wood surface were captured by recorded with a digital camera until the liquid seeps on the surface of the wood. Each of the captured video images was cut to an individual image at intervals of 10 seconds for the duration of 180 seconds. The contact angle of each image piece was then measured using Metric Images Plus (MIP) software to obtain an equilibrium contact angle (θ_e) based on the change in time. The contact angles of each droplet were measured both on the right and left side then the values were averaged (Figure 1).

The value of θ_e was measured using a segmented regression model with PROC NLIN software from SAS 9.1.3 Portable with the formula $y = a + bX + cX^2 + E$ where $x = \text{time}$; $y = \text{contact angle}$; a , b and $c =$

constant; and $E = \text{error}$. The constant change in contact angle (K -value) is calculated using the least-squares method according to the S/G equation using XL-STAT.

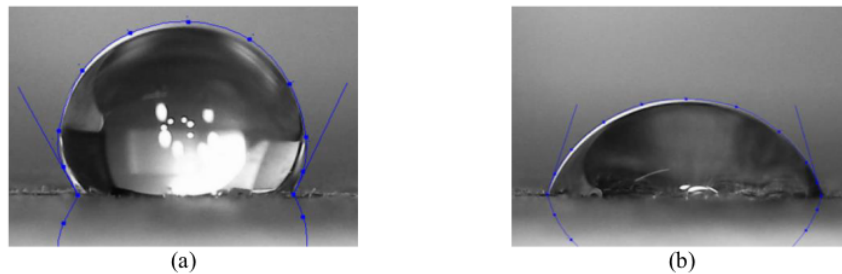


Figure 1. Measurement of the contact angle when water touches (a) and seeps (b) on the wood surface

2.2. Treatability measurements

The treatability samples were made in 10 pieces of sengon beams in dimension of 35 x 5 x 5 cm (longitudinal x tangential x radial) then air-dried in a room (temperature $29 \pm 12^{\circ}\text{C}$; RH $85 \pm 2.2\%$) for 10 days. All samples were then dried in an oven ($60^{\circ} \pm 1.5^{\circ}\text{C}$) until the moisture content decreased to $\pm 12\%$, then the dimensions (width, thickness, length) were measured and the initial weight was weighed. Both ends of each samples (± 2 cm) were immersed in hot paraffin. The samples were then soaked in a preservative for 24 hours at room temperature (cold soaking preservation methods). The preservative used is a combination of biocide insecticide (formulation: Cypermethrine 100 EC) and biocide wood fungicide (formulation: TCMTB) preservatives. These preservatives are used because wood deterioration is generally caused by high species of insects and fungi. After the preservation process, the sample is drained and then its final weight is weighed. Furthermore, the measurement of retention and penetration of preservatives is carried out with the following formula.

$$R = \frac{W1 - W0}{V} \text{ gr/cm}^3 \dots\dots\dots(1) \quad P = X1 + X2 + X3 + X4 \dots\dots\dots(2)$$

where R is Retention of preservatives (gr/cm^3); W1 is Weight of sample after preservation process (gr); W2 is Sample weight before preservation process (gr); V is Volume of sample after preservation process (cm^3); P is Penetration of preservative (mm); and X1 - X4 is Depth of entry of preservative on each side (mm).

3. Results and Discussions

3.1. Wettability measurements

Wettability is change in the contact angle that occurs with a change in time [22]. The wettability of wood is affected by the contact angle between the wood surface and the liquid. The liquid on the wood will spread and penetrate the wood until it is constant (θ_e). The value of θ_e is used to calculate the rate of change of constant contact angle (K -value). The smaller the value of θ_e of wood, the better its wettability. The average value of θ_e in 3 radial and 3 tangential sections is shown in Figure 2. The average value of θ_e produced by the radial section is higher than the tangential section. The average value of θ_e generated in the radial section is 18.70, 16.43, and 15.52, respectively. Meanwhile, the average value of θ_e produced in the tangential section is 12.36°, 12.78°, and 12.39°, respectively. The smaller the value of contact angle indicates the easier the material is wetted and vice versa [23]. The wettability of wood can be seen from the change of the

constant contact angle (K -value). The average K -values (Figure 2) generated on the radial sections are 0.23, 0.21, and 0.20, respectively, while the average K -values generated on the tangential sections are 0.32, 0.34, and 0.33, respectively. The higher the K -value, the better the wettability, meaning that it is easier for the liquid to spread on the surface of the wood substrate and penetrate faster into the wood [20, 24].

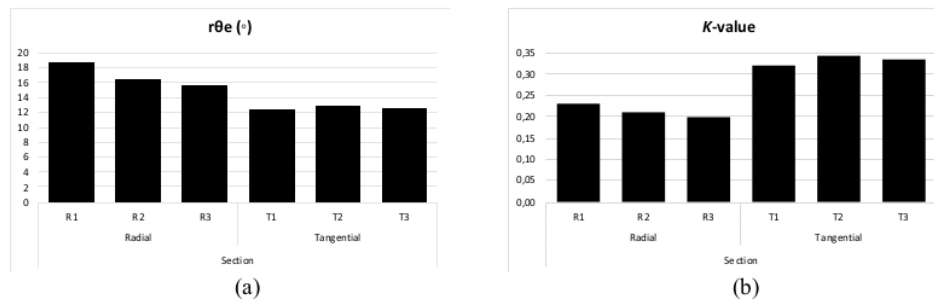


Figure 2. The average value of θ_e (a) and the average of K -value (b) of sengon wood

The results of the K -value measurement on sengon wood show that the tangential section has a higher wettability than the radial section. This is thought to be influenced by a lower contact angle on the tangential section caused the liquid spread and penetrated easier in its surface. However, these results indicate that there is no significant difference between the cross-sectional of wood in sengon wood. Liquids have the same wettability trend between radial and tangential cross-sectional patterns [8, 16, 25]. The adhesion on wood can be influenced by the surface texture and the direction of the fiber [23-28].

3.2. Treatability measurements

The treatability of sengon wood with a combination of biocide insecticide and biocide wood fungicide preservatives were shown in Table 1. The results showed that the average retention and penetration in sengon wood is 11,03 kg/m³ and 7,33 mm respectively. The penetration and retention values of sengon wood produced in this study were quite high, so it can be concluded that sengon wood is easy to preserve. This is presumably due to the low density of the sengon wood, which is 0.35-0.49 [29]. The low density of sengon wood can be explained by the high percentage of juvenile wood and high lumen diameter [30]. This is what is thought to cause preservatives to easily seep into the wood. Based on the results of these measurements, sengon wood has met SNI 03-5010.1-1999 (wood preservation for housing and buildings).

Table 1. The treatability of sengon wood with a combination of biocide insecticide and wood fungicide

Sample	Retention (Kg/m ³)	Penetration (mm)	Sample	Retention (Kg/m ³)	Penetration (mm)
1	11,24	7,42	7	10,85	6,95
2	10,89	8,03	8	10,79	6,9
3	10,82	7,15	9	11,74	7,25
4	11,89	6,87	10	11,77	7,31
5	10,36	7,59	Average	11,03	7,33
6	9,93	7,82			

4. Conclusions

18
The wettability of sengon is high with θ_e of 16.88 in the radial section and 12.51 in the tangential section. This shows that sengon wood has a good adhesion system for preservation. The results indicate that there is no significant difference between the cross-sectional of wood in sengon wood. Treatability of sengon wood showed that the average retention and penetration in sengon wood is 11,03 kg/m³ and 7,33 mm respectively. Based on the results of these measurements, sengon wood has met SNI 03-5010.1-1999 (wood preservation for housing and buildings) and can be used in wood working and biocomposite industries as the raw material such as Glued Laminated Wood (glulam), Laminated Veneer Lumber (LVL), etc.

References

- [1] Forest Watch Indonesia and Global Forest Watch 2002 *The State of the Forest: Indonesia* Bogor, Indonesia: Forest Watch Indonesia, and Washington DC: Global Forest Watch
- [2] Zastocki D, Oktaba J, and Lachowicz H 2021 Changes in the Market of Precious Wood: A Case Study of Submission System in Poland *Forests* **12** (421) pp 1-8 <https://doi.org/10.3390/f12040421>
- [3] Setiawan S, Barus B, and Suwardi 2014 Potential Analysis of the Community Forest Development in Central Lombok Regency *Majalah Ilmiah Globe* **16** (1) pp 69-76
- [4] Subarudi 2014 Development of Community Forest in Nusa Tenggara Barat Province and Its Wood Price Estimation *Forestry Socio and Economic Research Journal* **11** (3) pp 199-209
- [5] Abdurachman and Hadjib N 2006 Pemanfaatan hutan rakyat untuk komponen bangunan *Prosiding Seminar Hasil Litbang Hasil Hutan* Bogor pp 130-48
- [6] Delucis RA, Cademartori PHG, Missio AL, and Gatto DA 2016 Decay resistance of four fast-growing Eucalypts wood exposed to three types of fields *Maderas Cienc Tecnol* **18** (1) pp 33-42
- [7] Karlinasari L, Lestari AT, and Priadi T 2018 Evaluation of surface roughness and wettability of heat-treated, fast-growing tropical wood species sengon (*Paraserianthes falcataria* (L.) IC Nielsen), jabon (*Anthocephalus cadamba* (Roxb.) Miq.), and acacia (*Acacia mangium* Willd.) *Int. Wood Products Journal* pp 1-7
- [8] Lestari AT, Darmawan W, and Nandika D 2016 Effects of Surface Conditions on the Adhesion Strength of Surface Coatings *Jurnal Ilmu Teknologi Kayu Tropis* **14** (1) pp 11-22
- [9] Lestari AT, Darmawan IW and Nandika D 2020 Natural weathering on coated tropical woods IOP Conference Series: Material Science Engineering **935** 012067
- [10] Gray V 1962 *The wettability of wood* *Forest Product Journal* **12** (9) pp 452-461
- [11] Rathke J, and Sinn G 2013 Evaluating the wettability of MUF resins and pMDI on two different OSB raw materials *European Journal of Wood and Wood Products* **71** (3) pp 335-342
- [12] Ashokkumara S, Adler-Nissen J, and Møller P 2012 Factors affecting the wettability of different surface materials with vegetable oil at high temperatures and its relation to cleanability *Applied Surface Science* **263** pp 86-94
- [13] Tsoumis G 1991 *Science and technology of wood: Structure, Properties, Utilization* New York: Van Nostrand Reinhold
- [14] Yuan Y and Lee TR 2013 *Contact Angle And Wetting Properties* *Surface Science Techniques*, Springer pp 3-34
- [15] Bamber RK and Burley J 1983 *The Wood Properties of Radiate Pine* (Oxford: CAB) pp 84
- [16] Lestari AT 2020 Wettability on Tangential and Radial Surface of Rajumas Wood (*Duabanga moluccana* Blume) *Jurnal Perennial* **16** (1) pp 7-10
- [17] Demirci Z, Somnez A, and Budakci M 2013 Effect of Thermal Ageing on the Gloss and the Adhesion Strength of the Wood Varnish Layers *Bioresources* **8** (2) pp 1852-67
- [18] Esteves BM and Pereira HM 2009 *Wood modification by heat treatment: a review* *BioResources* **4** (1) pp 370-404

- [19] Tarmian A, Zahedi Tajrishi I, Oladi R, and Efhamisisi D 2020 Treatability of wood for pressure treatment processes: a literature review. *European Journal of Wood and Wood Products* **78** pp 635-660 <https://doi.org/10.1007/s00107-020-01541-w>
- [20] [ASTM] American Society for Testing and Materials 2004 ASTM D 358-98: *Standard Specification for Wood to Be Used as Panels in Weathering Tests of Coatings* (West Conshohocken: ASTM)
- [21] Li J, Li B, Zhang J, and Zhou X 2019 Tannin Resins for Wood Preservatives: A Review *Research and Application of Materials Science Journal* **1** (1) 45-48
- [22] Shi SQ and Gardner DJ 2001 Dynamic adhesive wettability of wood *Wood and Fiber Science* **33** (1) pp 58-68
- [23] Petrie EM 2000 *Handbook of Adhesive and Sealants*. United States (US): McGraw-Hill
- [24] Martha R, Dirna FC, Hasanusi A, Rahayu IS, and Darmawan W 2020 Surface free energy of 10 tropical woods species and their acrylic paint wettability *Journal of Adhesion Science and Technology* **34** (2) pp 167-177 doi: 10.1080/01694243.2019.1663009
- [25] Amorim MRS, Ribeiro PG, Martins SA, Del Menezzi CHS, and Souza MR 2013 Surface wettability and roughness of 11 amazonian tropical hardwoods *Floresta e Ambiente* **20** (1) pp 99-109
- [26] Williams RS, Knaebe MT, and Feist WC 1996 *Finishes for Exterior Wood* (Madison: Forest Products Laboratory)
- [27] Ayrilmis N, Candan Z, Akbulut T, and Balqiz OD 2010 Effect of sanding on surface properties of medium density fiberboard *Drvna Industrija* **61**(3) pp 175-81
- [28] Darmawan W, Rahayu IS, Padlinurjaji IM, and Pandit KN 2011 *Pengerjaan Kayu: Ilmu-Ilmu Penunjang dan Teknologi Proses* (Bogor: IPB Pr.)
- [29] Hartati S, Sudarmonowati E, Patriasari W, Hermiati E, Dwianto W, Kaida R, Baba K, and Hayashi T 2010 Wood Characteristic of Superior Sengon Collection and Prospect of Wood Properties Improvement through Genetic Engineering *Wood Research Journal* **1** (2) pp 103-107
- [30] Fajriani E, Ruelle J, Dlouha J, Fournier M, Hadi Y, and Darmawan W 2013 Radial variation of wood properties of Sengon (*Paraserianthes falcataria*) and Jabon (*Anthocephalus cadamba*) *Journal of the Indian Academy of Wood Science* **10** (2) pp 110-117 doi:10.1007/s13196-013-0101-z

ORIGINALITY REPORT

23%
SIMILARITY INDEX

%
INTERNET SOURCES

23%
PUBLICATIONS

%
STUDENT PAPERS

PRIMARY SOURCES

1 U Adzkia, I S Rahayu, L Karlinasari. " The effect of pre-freezing treatment on the color changes and wettability of teak wood (Linn.F.) ", IOP Conference Series: Materials Science and Engineering, 2020 **3%**
Publication

2 Lina Karlinasari, Andi Tri Lestari, Trisna Priadi. " Evaluation of surface roughness and wettability of heat-treated, fast-growing tropical wood species sengon ((L.) I.C.Nielsen), jabon ((Roxb.) Miq), and acacia (Willd.) ", International Wood Products Journal, 2018 **3%**
Publication

3 Yusuf Sudo Hadi, Dede Hermawan, Ignasia Maria Sulastiningsih, Efrida Basri, Gustan Pari, Rohmah Pari, Imam Busyra Abdillah. "Color Change and Physical-Mechanical Properties of Polystyrene-Impregnated Glulam from Three Tropical Fast-Growing Wood Species", Forests, 2021 **3%**
Publication

4

B H Kusumo, S Sukartono, B Bustan, Y A Purwanto. "Total nitrogen in rice paddy field independently predicted from soil carbon using Near Infrared Reflectance Spectroscopy (NIRS)", *Journal of Physics: Conference Series*, 2019

Publication

2%

5

A A Birrnaqiy, Basyaruddin, J Malik. "Impregnation analysis of phenol-formaldehyde resin on sengon wood to explore the potential of sengon wood as construction material", *IOP Conference Series: Earth and Environmental Science*, 2022

Publication

2%

6

Qinglin Yu, Xi Pan, Zhong Yang, Li Zhang, Jingyun Cao. "Effects of the Surface Roughness of Six Wood Species for Furniture Production on the Wettability and Bonding Quality of Coating", *Forests*, 2023

Publication

2%

7

Xianai Huang, Duygu Kocaefe, Yaman Boluk, Yasar Kocaefe, Andre Pichette. "Einfluss der Oberflächenbearbeitung auf die Benetzbarkeit von thermisch behandeltem Kiefernholz (Jack Pine) mit verschiedenen Flüssigkeiten", *European Journal of Wood and Wood Products*, 2012

Publication

1%

8

Efrida Basri, Nisrina Hanif, Resa Martha, Istie S. Rahayu, Wayan Darmawan, Philippe Gérardin. "Effect of Non-Biocide Chemical and Thermal Modifications on Stability and Durability of Short Rotation Teak Wood from Plantation", Research Square Platform LLC, 2022

Publication

1 %

9

Yusuf Hendrawan, Nisrina Sajidah, Choirul Umam, Muchammad Riza Fauzy, Yusuf Wibisono, La Choviya Hawa. " Effect of Carbonization Temperature Variations and Activator Agent Types on Activated Carbon Characteristics of Sengon Wood Waste () ", IOP Conference Series: Earth and Environmental Science, 2019

Publication

1 %

10

Asghar Tarmian, Ismaeil Zahedi Tajrishi, Reza Oladi, Davood Efhamisisi. "Treatability of wood for pressure treatment processes: a literature review", European Journal of Wood and Wood Products, 2020

Publication

<1 %

11

Bekir Cihad Bal. "Physikalische und mechanische Eigenschaften von thermisch modifiziertem juvenilem und adultem Schwarzkiefernholz", European Journal of Wood and Wood Products, 2013

<1 %

12

E Rahail, Untari, I Herdjiono, Saadah, C Wahyuni, T Dariati. "Low-emission strategy through effective planning and public participation in Merauke", IOP Conference Series: Earth and Environmental Science, 2019

Publication

13

Milojka Gindl, Stefanie Tschegg. "Significance of the Acidity of Wood to the Surface Free Energy Components of Different Wood Species", Langmuir, 2002

Publication

14

Evren Osman Çakıroğlu, Aydın Demir, İsmail Aydın, Ümit Büyüksarı. "Prediction of optimum CNC cutting conditions using artificial neural network models for the best wood surface quality, low energy consumption, and time savings", BioResources, 2022

Publication

15

L Karlinasari, U Adzkie, R A Tang, Irzaman. "Dielectric properties of heat treated teak wood (*Tectona grandis* Linn. F)", IOP Conference Series: Materials Science and Engineering, 2020

Publication

16

Mohd Khairun Anwar Uyup, Lee Seng Hua, Alia Syahirah Yusoh, Asniza Mustapha, Siti

<1 %

<1 %

<1 %

<1 %

<1 %

Norasamah Surip. " Wettability of keruing (spp.) wood after weathering under tropical climate ", Physical Sciences Reviews, 2022

Publication

17

Nisrina P. Hanifah, Resa Martha, Istie S. Rahayu, Wayan Darmawan, Béatrice George, Philippe Gérardin. "Surface characterization and paint bonding quality on chemically and thermally modified short rotation teak wood", International Wood Products Journal, 2022

Publication

<1 %

18

Roberto Daniel de Araujo, Joaquim dos Santos, Claudete Catanhede do Nascimento, Cristiano Souza do Nascimento et al. "Surface roughness of edge glued panels (EGP) of amazon managed species", Ciência e Agrotecnologia, 2019

Publication

<1 %

19

Yusuf Sudo Hadi, Muh Yusram Massijaya, Lukmanul Hakim Zaini, Rohmah Pari. "Physical and Mechanical Properties of Methyl Methacrylate-Impregnated Wood from Three Fast-Growing Tropical Tree Species", Journal of the Korean Wood Science and Technology, 2019

Publication

<1 %

20

María Graciela Aguayo, Oswaldo Erazo, Claudio Montero, Laura Reyes, William

<1 %

Gacitúa, Liset Gómez, Hugo Torres. "Analyses of Impregnation Quality and Mechanical Properties of Radiata Pine Wood Treated with Copper Nanoparticle- and Micronized-Copper-Based Wood Preservatives", *Forests*, 2022

Publication

21

Z Arifin, S Sukartono, L E Susilawati, B H Kusumo, I Yasin. "Performance of maize under two different methods of fertilizer application in semi-arid tropic Dompu Indonesia", *Journal of Physics: Conference Series*, 2019

Publication

22

Jianxin Cui, Zehui Ju, Lu Hong, Biqing Shu, Xiaoning Lu. "Hydrophobic Poplar Prepared via High Voltage Electric Field (HVEF) with Copper as Electrode Plate", *Journal of Renewable Materials*, 2022

Publication

23

Bansal, Priyanka. "Water-Based Polymeric Nanostructures for Agricultural Applications", *Philipps-Universität Marburg*, 2010.

Publication

24

Ros Syazmini Mohd Ghani. "A review of different barriers and additives to reduce boron movement in boron dual treated wood", *Progress in Organic Coatings*, 2021

Publication

<1 %

<1 %

<1 %

<1 %

25

Svenja K Reinke, Katharina Hauf, Josélio Vieira, Stefan Heinrich, Stefan Palzer. "Changes in contact angle providing evidence for surface alteration in multi-component solid foods", *Journal of Physics D: Applied Physics*, 2015

Publication

<1 %

Exclude quotes On

Exclude matches Off

Exclude bibliography On

2021_IOP_Tri_Wettability_Sengon_Scopus_Q4.pdf

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7
